

# Polymer Chemistry

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: F. Lugo, L. Trossaert, Y. Marien, M. Sabbe, M. Edeleva, D. R. D'hooge and P. Van Steenberge, *Polym. Chem.*, 2025, DOI: 10.1039/D5PY00343A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

# Pulsed laser polymerization to retrieve kinetic parameters for a propagated mid-chain radical in poly(*n*-butyl acrylate) synthesis: a combined DFT and kinetic Monte Carlo study

F.A. Lugo<sup>2</sup>, L. Trossaert<sup>1,2</sup>, Y.W. Marien<sup>1,3</sup>, M.K. Sabbe<sup>1</sup>, M. Edeleva<sup>2</sup>, D.R. D'hooge<sup>1,4\*</sup>, P.H.M. Van Steenberge<sup>1</sup>

1. Laboratory for Chemical Technology (LCT), Ghent University, Technologiepark 125, B-9052 Gent, Belgium.
2. Centre for Polymer and Material Technologies (CPMT), Ghent University, Technologiepark 130, B-9052 Gent, Belgium.
3. Intelligence in Processes, Advanced Catalysts and Solvents (iPRACS), Faculty of Applied Engineering, University of Antwerp, Groenenborgerlaan 171, 2020 Antwerp, Belgium.
4. Centre for Textile Science and Engineering (CTSE), Ghent University, 70a, B-9052 Gent, Belgium.

Corresponding author: dagmar.dhooge@ugent.be

## Abstract

Radical polymerization of *n*-butyl acrylate is characterized by backbiting of end-chain radicals (ECRs), with a propagation rate coefficient  $k_{p,e}$ , into mid-chain radicals (MCRs), with a propagation rate coefficient  $k_{p,m}$ . In pulsed laser polymerization (PLP) kinetic studies, it is currently assumed that a MCR becomes a (fully developed) ECR after one propagation step. Here we demonstrate that a more gradual transition likely takes place, introducing a propagated mid-chain radical (PMR) with a propagation rate coefficient  $k_{p,p}$  or equivalently a transition propagation factor  $\gamma$  that at least theoretically can vary between 0 ( $k_{p,p}=k_{p,m}$ ) and 1 ( $k_{p,p}=k_{p,e}$ ). Kinetic Monte Carlo (kMC) simulations under free radical polymerization (FRP) conditions hint at a  $\gamma$  not too close to 0 (e.g. not below 0.01), and Density functional theory (DFT) calculations at a  $\gamma$  not too close to 1 (e.g. not above 0.8). It is further shown that the ratio of the peak heights in a PLP – size exclusion chromatography (PLP-SEC) spectrum is sensitive to a variation in  $\gamma$ . This opens the door to the future experimental determination of  $k_{p,p}$  considering different frequencies, provided that the initiator radical generation is well-described. At 325 K and using 500 Hz literature data, we currently put forward a  $\gamma$  of 0.1. In addition, the PMR backbiting potential is evaluated, introducing a backbiting scaling factor  $\beta$  with respect to the conventional ECR backbiting rate coefficient ( $k_{bb}$ ). It is showcased that this extra backbiting contributes to a better understanding of the migration mechanism and short branch formation in acrylate radical polymerization, although the experimental determination of  $\beta$  is less straightforward. Overall the current work highlights how acrylate-specific rate coefficients can be obtained in a roadmap format, considering higher and lower frequencies, and lower and higher temperatures.

**Keywords:** acrylics; branching; rate coefficients; photoinitiator; backbiting



## Introduction

View Article Online  
DOI: 10.1039/D5PY00343A

Free radical polymerization (FRP) is a widely used technique for the production of polyacrylics such as polyacrylates [1-5]. Such polymers are nowadays manufactured using a large variety of (co)monomers, both fuel- and biomass-based, making them very suitable for material optimization and property tuning [1, 6-12]. However, for a given polyacrylate to suit a certain application, a proper tuning of the molecular properties (e.g. molar mass distribution (MMD) or branching level) is desired. This is non-trivial as polyacrylate synthesis displays a complicated reaction scheme, dealing with multiple secondary reactions next to the conventional FRP reactions, e.g. initiation, (secondary) propagation, and termination. A detailed mechanistic understanding of acrylate polymerization is thus not straightforward and kinetic modeling is a desired pathway, provided that the (intrinsic) rate coefficients of all kinetically relevant reactions are carefully determined [13-17].

A well-established technique for the determination of rate coefficients in radical polymerization is pulsed laser polymerization (PLP) in combination with size exclusion chromatography (SEC) [18]. Aleksandrov et al. [19] originally studied kinetic and MMD variations in PLP. Later on Olaj et al. [20] extended the technique to obtain the propagation rate coefficient from the log-MMD. Additionally, the technique is recommended by the IUPAC Subcommittee on Modeling of Polymerization Kinetics and Processes [21-27].

PLP employs a laser beam to create pulse-wise initiator radicals, most commonly 2,2-dimethoxy-2-phenylacetophenone (DMPA) fragments, that initiate radical chain growth [28, 29]. During the time between two laser pulses, which is called the dark time  $\Delta t$ , (macro)radicals grow and some of them terminate at the next pulse via the freshly generated initiator fragments in a kind of quenching manner [30].

If only a (conventional) end-chain radical (ECR) is active as a macroradical in a PLP experiment, the chain length of specific dead polymer species ( $L_j$ ) will therefore depend on the number of pulses ( $j$ ),  $\Delta t$ , the initial monomer concentration ( $[M]_0$ ), and the ECR propagation rate coefficient  $k_{p,e}$ :

$$L_j = k_{p,e}[M]_0(j\Delta t) \quad (1)$$

Practically,  $L_1$  is the first inflection point (or peak maximum) of the SEC trace ( $j = 1$ ) [31-35], and  $L_2$  provides a consistency check because it needs to be equal to twice  $L_1$  [21, 36].

In general, the subscript “app” should be used in Equation 1 to highlight that several macroradical types can exist, each with a distinct (intrinsic) propagation reactivity, together leading to an observed thus lumped/apparent propagation reactivity ( $k_{p,app}$ ). For example, in high temperature acrylate radical polymerization  $k_{p,app}$  does not equal  $k_{p,e}$ . Mid-chain radicals (MCRs) are then also present, undergoing slower (tertiary) propagation (rate coefficient:  $k_{p,m}$ ). Mechanistically, the formation of MCRs out of ECRs mainly proceeds through intramolecular chain transfer, *i.e.* backbiting. This reaction proceeds most easily via a six-membered transition state, leading to the creation of polymer chains with short side chain branches upon further (tertiary) propagation [37-40].

The existence of ECRs and MCRs (top of Figure 1) in acrylate radical polymerization moves the SEC trace to the lower chain length region, due to a lower  $k_{p,m}$  [40-47], which can be understood considering the bulkier and more carbon substituted nature of the MCR and the difference in stability between both radical types. In other words, whenever backbiting occurs and a MCR is formed, a decrease of  $k_{p,app}$  takes place because a MCR propagates at a slower rate [17]. At sufficiently high temperatures macromonomers are also formed, due to fragmentation ( $\beta$ -scission) of MCRs [48, 49].



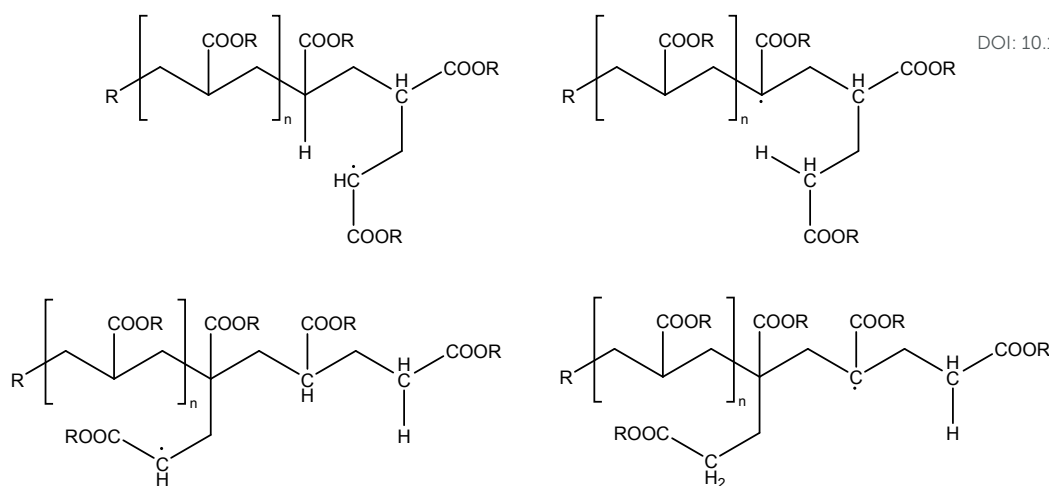
View Article Online  
DOI: 10.1039/D5PY00343A

Figure 1: Top: End-chain radical (ECR) for acrylate radical polymerization (left); mid-chain radical (MCR) formed through backbiting over a six-membered transition state out of this ECR (right). Bottom: (left) Extra species explored in the present work, being a propagated mid-chain radical (PMR) as well (right) a new MCR after backbiting of this PMR.

Notably, the influence of certain secondary reactions such as backbiting can be minimized by adapting the PLP conditions. A low temperature and high laser pulse frequency enable for instance an accurate (isolated) determination of  $k_{p,e}$ , as highlighted by Willemse and van Herk [50], who studied the secondary propagation of methyl, ethyl, butyl, hexyl and benzyl acrylate at frequencies between 60 and 100 Hz and temperatures between -25 to 37 °C. Even higher frequencies, i.e. 500 Hz and 1 kHz, have been used for PLP of *n*-butyl acrylate by Barner-Kowollik *et al.* [30] and Wenn and Junkers [51] respectively. Once  $k_{p,e}$  is known, a stepwise modification of the (isothermal) PLP conditions can be done to determine other (secondary) rate coefficients ideally one by one, enabling to span a detailed reaction scheme [30, 43, 52, 53].

Recent work by Marien *et al.* [54] and Vir *et al.* [18] showed that the rate coefficients for backbiting, MCR propagation and  $\beta$ -scission can be determined through stepwise PLP combined with kinetic Monte Carlo (*k*MC) simulations once  $k_{p,e}$  is known. The first step consists of varying frequencies in the low frequency region (e.g. 10 to 50 Hz) at low to intermediate temperature while also varying the solvent fraction, selecting as solvent the saturated analogue of the monomer. Under these conditions  $\beta$ -scission is negligible, so that an isolation of the backbiting rate coefficient ( $k_{bb}$ ) and  $k_{p,m}$  is possible. The second step follows the same procedure of varying frequencies and solvent fractions but deals with higher temperatures to determine the  $\beta$ -scission rate coefficient ( $k_{\beta}$ ), inputting previously determined  $k_{p,e}$ ,  $k_{bb}$  and  $k_{p,m}$  values.

Another experimental technique commonly used for the determination of rate coefficients in radical polymerization is the combination of PLP with Electron Paramagnetic Resonance (PLP-EPR) [55, 56]. This technique involves measuring the intensity of an EPR signal as a function of time, and from this, deducing concentration as a function of time for the radical species giving rise to the measured signal, whether it be ECR or MCR, both of which may be monitored simultaneously. The EPR measurement is often combined with PLP because it allows for control over the amount of radicals produced; specifically in certain cases authors used a single-pulse for these PLP-EPR experiments [57-68].

Note that it is implicitly assumed in the current acrylate (PLP) modeling studies that a MCR becomes an ECR after one propagation step, although the computational chemistry work of Cuccato *et al.* [69] for instance indicated a possible difference in propagation reactivity of a single-unit short branched polymer. Such difference has been related to the bulkier nature of the involved radical, in the current



work denoted as a propagated mid-chain radical (PMR; Figure 1; bottom left), as compared to a well-developed ECR, *i.e.* one possessing a radical center that is several monomer units away from the original MCR backbone. Similarly, chain length dependencies have been reported for the activation of halogen-capped tertiary radical chains in atom transfer radical polymerization (ATRP) involving methacrylates, due to an entropic strain effect [70]. Also, for radical polymerizations with only ECRs, a different propagation rate coefficient for the first two to ten additions has been reported [71].

In the present work, we enrich the PLP-SEC modeling analysis of acrylates by studying the kinetic and structural relevance of the transition from a MCR to a PMR, and this PMR to a (developed) ECR. We also perform density functional theory (DFT) simulations [69, 72-79] complementary with the work of Cuccato *et al.* [69], and we discuss PMR backbiting possibilities (new rate coefficient  $k_{bb,P}$ ), producing different types of branches and contributing to radical migration (Figure 1; bottom right).

Practically, we calculate the PMR propagation rate coefficient,  $k_{p,P}$ , using a transition propagation factor  $\gamma$ , and we calculate  $k_{bb,P}$  via a scaling factor  $\varphi$ :

$$k_{p,P} = (k_{p,e} - k_{p,m})\gamma + k_{p,m} \quad (2)$$

$$k_{bb,P} = \varphi k_{bb} \quad (3)$$

Hence, for  $\gamma$  equal to 0,  $k_{p,P} = k_{p,m}$  results, for  $\gamma$  equal to 1  $k_{p,P} = k_{p,e}$  (the current assumption), and for  $\varphi$  equal to 1  $k_{bb,P} = k_{bb}$ .

A mechanistic foundation is put forward hinting at  $\gamma$  and  $\delta$  values not being too close to 1, to then demonstrate that in future work  $\gamma$  could be experimentally determined by measuring peak height ratios in the PLP spectrum, taking into account a frequency variation and relying on a good determination of radical generation kinetic parameters (at lower temperatures). Focusing at FRP conditions, we also highlight that  $\gamma$  is (likely) sufficiently higher than 0 (e.g.  $\gg 0.01$ ), supporting current parameter tuning efforts from all IUPAC connected groups for  $k_{p,m}$  and  $k_{bb}$  ignoring the PMR species. Based on literature data at one frequency we assess  $\gamma$  as 0.1 at 325 K in the present work. For  $\delta$ , however, only a rough estimate is possible in future work considering PLP branching data.

Overall this work contributes to the identification of a better roadmap for the determination of the (intrinsic) reactivities of acrylate specific reaction steps, and the type of branched species present. We complement the current modeling studies by a refinement of the kinetic scheme in case more detailed branching descriptions are aimed at.

## Methods

### Computational chemistry details

DFT calculations were performed using the Gaussian 16\_C.01 package [80]. The molecular model structures were optimized at the B3LYP/6-311+G(d,p) method and basis set. The thermal contributions were included using the harmonic oscillator approach at the same computational level. The structures used were confirmed to have zero imaginary frequencies for reactants and products, and one large imaginary frequency in the transition states. The prediction of the electronic energy was improved by using a single-point M06-2X/6-311+G(d,p) calculation employing the previously optimized geometries.

To calculate enthalpies, entropies and free Gibbs energies in the gas phase, standard thermodynamic equations were used [81]. Solvation effects were included using COSMO-RS theory [82-84] to calculate the free Gibbs energy of solvation  $\Delta G_{solv}$ , as implemented in the COSMOtherm software package [85].



The COSMO-RS calculation uses the electronic energy calculated by BP86/TZVP single point calculations performed on the previously B3LYP/6-311+G(d,p) optimized geometry, using the density of *n*BuA at 298 K of 894 g L<sup>-1</sup>.

The transition state theory (TST) was used to calculate the rate coefficients, using the free Gibbs reaction barrier including solvation effects [86, 87]:

$$k(T) = \kappa(T) \frac{k_B T}{h} (C^0)^{-\Delta^\ddagger n} \exp\left(-\frac{\Delta^\ddagger G_{cond}^0}{RT}\right) \quad (4)$$

in which  $\kappa$  is the quantum tunneling correction factor calculated via the Eckart method [88],  $k_B$  is the Boltzmann constant,  $h$  the Planck constant,  $C^0$  the standard concentration,  $\Delta^\ddagger n$  the difference in moles between reactant and transition state,  $\Delta^\ddagger G_{cond}^0$  the temperature-dependent free Gibbs energy barrier, and  $R$  the universal gas constant.

We calculated the propagation rate coefficient for PMR,  $k_{p,p}$ , using the molecular model depicted in Figure 2 (top). This model consists of a tetramer radical, which represents the intermediate between a MCR and ECR, propagating toward a monomer unit and forming the pentamer branched structure shown in Figure 2 (top right). The use of multiple diastereomers, as incorporated in previous work, was unnecessary for this model, because the influence of the stereochemistry of adjacent units on the rate coefficient in propagation reactions is minimal [74]. Furthermore, the computational effort, required to calculate the large structures of the model, can be significantly reduced by using a single diastereomer, making the calculations more feasible.

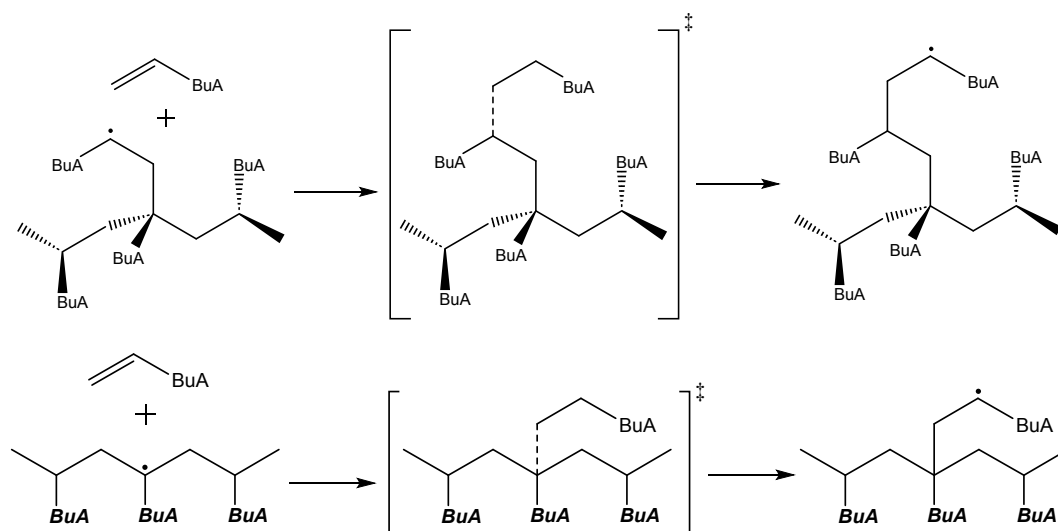


Figure 2. Top: Molecular model used to predict the propagation rate coefficient of the propagated mid-chain radical (PMR). It consists of a tetramer radical, propagating towards a monomer. Bottom: Molecular model used to predict the propagation rate coefficient of the mid-chain radical (MCR). It consists of a trimer radical, propagating towards a monomer.

Similarly, the MCR propagation rate coefficient,  $k_{p,m}$ , was calculated using the molecular model shown in Figure 2 (bottom), which consist of a symmetric trimer *n*BuA structure with a radical in the middle unit, propagating towards a *n*BuA monomer. We employed a single diastereomer for this calculation, as the reaction represents an equivalent propagation process with no significant influence from the stereochemistry of adjacent units.

The rate coefficient for the ECR propagation,  $k_{p,e}$ , was calculated using a model consisting of a unimer radical propagating towards a monomer *n*BuA unit.





Besides DFT analysis, it can be interesting to look at spectroscopic experimental techniques that can prove or measure details about the PMR radical. One technique could be EPR, which can detect different radicals within a system. However, the subtle structural difference between an ECR and a PMR might not be distinguishable by this technique, because in essence, both of these radicals are secondary radicals and the difference arises from the different nearby substituents. One can only hypothesize about which effect is greater than the other. In Kajiwara's work [89-91], the noisy spectrum at lower temperatures might be a result of the subtle differences between ECR and PMR, but nobody has looked for these species before because the PMR has not been discussed previously. Another technique might be detection by nuclear magnetic resonance (NMR). However, the applicability of this technique comes likely with various challenges because polymer samples produce a high signal-to-noise ratio, due to the existence of the large  $-\text{CH}_2-$  signal. Hence, overall DFT is expected to be the easiest way to study the qualitative differences between ECR and PMR.

### **Kinetic Monte Carlo model details**

For the prediction of the complete PLP-SEC trace and inflection point data, the previously developed kinetic Monte Carlo (*k*MC) model of our group was utilized as a starting point [18, 28, 34, 54] but including the two extra reactions with PMR via the already introduced formulas for  $\gamma$  and  $\delta$  in the introduction (Equation (2) and Equation (3)). It is important to mention that adding two extra parameters to a modelling system provides extra flexibility regarding the description of experimental data. However, both these parameters,  $\gamma$  and  $\delta$ , are introduced to physically account for rate coefficients of species that likely have different reactivities because their chemical structures are different.

The *k*MC model considers a detailed reaction scheme, accounting for chain length (and monomer conversion) dependent apparent termination reactivities with all kinetic parameters taken from the literature (with  $\gamma = 1$ ). Under the conditions studied, namely a low temperature, a low monomer conversion and a high pulse rate,  $\beta$ -scission, macromonomer propagation and thermal self-initiation can be ignored [18].

The Arrhenius parameters for termination (and chain transfer to monomer) with PMR are approximated as if the radical was an ECR. Figure S1 of the Supplementary Information shows that the impact of PMR-based radical termination over the polymer properties is limited within the expected theoretical limits, being defined by mutual ECR termination and mutual MCR termination, supporting this approximation. Additionally, any previous determination of termination reactivities might have clumped the effect of the PMR in the reported values, making the approximation of PMR reactivity as an ECR quite suitable. If the PMR termination kinetics would be of more relevance, the introduction of another type of radical would complicate further the determination of termination rate coefficients. However, this radical will not dominate the amount of radicals within the PLP so it is not kinetically relevant in the context of the present work.

Taking into account the decrease in light intensity along the optical path [92], the amount of radicals produced by photodissociation ( $\Delta R_0$ ) is explicitly calculated [28, 34, 93, 94]:

$$\Delta[R_0] = 2\Phi \frac{E_{\text{pulse}}\lambda}{hcN_A V} [1 - \exp(-2.303\epsilon[I_2]L)] \quad (5)$$

in which  $\Phi$  is the quantum yield for photodissociation as ideally determined at low temperature with no kinetic relevance of PMR (and MCR) species,  $\lambda$  the wavelength of the laser,  $E_{\text{pulse}}$  the energy of a laser pulse,  $h$  the Planck constant,  $c$  the speed of light,  $N_A$  the Avogadro constant,  $V$  the volume of



the sample,  $[I_2]$  the photoinitiator concentration,  $\varepsilon$  the molar absorptivity, and  $L$  the optical path length. View Article Online  
DOI: 10.1039/D5PY00343A

Table 1: Reactions and respective Arrhenius parameters applied in the  $k$ MC model for PLP and FRP; note that for  $\gamma=1$  a PMR becomes an ECR, hence, the original model is obtained [18, 28, 34, 54].

nr	Reaction	Equation	A L mol <sup>-1</sup> s <sup>-1</sup> or s <sup>-1</sup>	E <sub>a</sub> kJ mol <sup>-1</sup>	k @ 306K L mol <sup>-1</sup> s <sup>-1</sup> or s <sup>-1</sup>	Ref.
1	Photo-dissociation <sup>a,b</sup>	$I_2 \xrightarrow{h\nu} R_{0,e}^I + R_{0,e}^{II}$				[18, 28]
2	Chain initiation <sup>c</sup>	$R_0^{I/III} + M \xrightarrow{k_{p,I/III}} R_{1,e}$	$2.4 \times 10^8$	17.9	$2.1 \times 10^5$	[25, 34, 95]
3	Propagation <sup>d</sup>	$R_{i,e} + M \xrightarrow{k_{p,e}} R_{i+1,e}$	$2.2 \times 10^7$	17.9	$1.9 \times 10^4$	[25]
4		$R_{i,m} + M \xrightarrow{k_{p,m}} R_{i+1,P}$	$1.94 \times 10^6$	28.3	$1.4 \times 10^1$	[18]
5		$R_{i,P} + M \xrightarrow{k_{p,P}} R_{i+1,e}$	$k_{p,P} = \gamma(k_{p,e} - k_{p,m}) + k_{p,m}$			<i>This work</i>
6	Backbiting	$R_{i,e} \xrightarrow{k_{bb}} R_{i,m}, i \geq 3$	$1.6 \times 10^8$	34.7	$1.9 \times 10^2$	[18]
7		$R_{i,P} \xrightarrow{k_{bb,P}} R_{i,m}, i \geq 3$	$k_{bb,P} = \delta k_{bb}$			<i>This work</i>
8	Chain transfer to monomer	$R_{i,e} + M \xrightarrow{k_{tr,m,e}} P_i + R_{0,e}^{III}$	$2.9 \times 10^5$	32.6	$7.8 \times 10^{-1}$	[96]
9		$R_{i,m} + M \xrightarrow{k_{tr,m,m}} P_i + R_{0,e}^{III}$	$2.0 \times 10^5$	46.1	$2.7 \times 10^{-3}$	[96]
10		$R_{i,P} + M \xrightarrow{k_{tr,m,P}} P_i + R_{0,e}^{III}$	$2.9 \times 10^5$	32.6	$7.8 \times 10^{-1}$	<i>This work</i>
11	Termination <sup>e</sup>	$R_{i,e} + R_{j,e} \xrightarrow{k_{t,app,i,j}^{e-e}} P_{i+j}$ $R_{i,e} + R_{j,e} \xrightarrow{k_{t,app,i,j}^{e-e}} P_i + P_j$	$1.3 \times 10^{10}$	8.4	$9.6 \times 10^8$	[97]
12		$R_{i,e} + R_{j,m} \xrightarrow{k_{t,app,i,j}^{e-m}} P_{i+j}$ $R_{i,e} + R_{j,m} \xrightarrow{k_{t,app,i,j}^{e-m}} P_i + P_j$	$4.2 \times 10^9$	6.6	$2.1 \times 10^8$	[97]
13		$R_{i,m} + R_{j,m} \xrightarrow{k_{t,app,i,j}^{m-m}} P_{i+j}$ $R_{i,m} + R_{j,m} \xrightarrow{k_{t,app,i,j}^{m-m}} P_i + P_j$	$9.0 \times 10^6$	5.6	$2.0 \times 10^6$	[97]
14		$R_{i,P} + R_{j,P} \xrightarrow{k_{t,app,i,j}^{P-P}} P_{i+j}$ $R_{i,P} + R_{j,P} \xrightarrow{k_{t,app,i,j}^{P-P}} P_i + P_j$	$1.3 \times 10^{10}$	8.4	$9.6 \times 10^8$	<i>This work</i>
15		$R_{i,P} + R_{j,e} \xrightarrow{k_{t,app,i,j}^{P-e}} P_{i+j}$ $R_{i,P} + R_{j,e} \xrightarrow{k_{t,app,i,j}^{P-e}} P_i + P_j$	$1.3 \times 10^{10}$	8.4	$9.6 \times 10^8$	<i>This work</i>
16		$R_{i,P} + R_{j,m} \xrightarrow{k_{t,app,i,j}^{P-m}} P_{i+j}$ $R_{i,P} + R_{j,m} \xrightarrow{k_{t,app,i,j}^{P-m}} P_i + P_j$	$4.2 \times 10^9$	6.6	$2.1 \times 10^8$	<i>This work</i>
17		$R_{0,e}^{I/III/III} + R_{0,e}^{I/III/III} \xrightarrow{k_{t,app,i,j}^{0-0}} P_0$	$1.3 \times 10^{10}$	8.4	$9.6 \times 10^8$	f
18		$R_{0,e}^{I/III/III} + R_{i,e} \xrightarrow{k_{t,app,i,j}^{0-e}} P_i + (P_0)$	$1.3 \times 10^{10}$	8.4	$9.6 \times 10^8$	g
19		$R_{0,e}^{I/III/III} + R_{i,m} \xrightarrow{k_{t,app,i,j}^{0-m}} P_i + (P_0)$	$4.2 \times 10^9$	6.6	$2.1 \times 10^8$	h
20		$R_{0,e}^{I/III/III} + R_{i,P} \xrightarrow{k_{t,app,i,j}^{0-P}} P_i + (P_0)$	$1.3 \times 10^{10}$	8.4	$9.6 \times 10^8$	i

<sup>a</sup> Initiator radicals (I and II) are different radicals created by the photodissociation of DMPA [34]. <sup>b</sup> For the FRP case, we use instead an initiator dissociation with the following kinetic parameters:  $A = 3.1 \times 10^{15} \text{ s}^{-1}$  and  $E_a = 131 \text{ kJ mol}^{-1}$  [98, 99]. For the PLP case the amount of initiator radicals produced by photodissociation in each laser pulse is calculated by Equation (5). Using  $\lambda = 351 \times 10^{-9} \text{ m}$ ,  $E_{pulse} = 2.5 \times 10^{-3} \text{ J}$ ,  $V = 2 \times 10^{-7} \text{ m}^3$  and  $L = 5.2 \times 10^{-3}$  [34],  $\Delta[R_0]$  equals  $4.8 \times 10^{-5} \text{ mol L}^{-1}$  at the first laser pulse. <sup>c</sup> The second radical of the initiator  $R_{0,II}$  is considered to not chain initiate. <sup>d</sup> Only the plateau value is shown for ECR propagation reactivity, chain length dependency is considered based on the work of Heuts and Russell [71], see Supplementary Information S2. <sup>e</sup> Chain length dependent apparent termination rates are considered (see Supplementary Information S2) [97]; only the apparent unimer rate coefficient is shown, taking into account a correction factor 2 [100]; the fraction of termination done by recombination is assumed 0.9 for entry 11, 17 and 18, 0.3 for entry 12 and 19, and 0.1 for entry 13, in agreement with literature data [101, 102]; one of the disproportionation products is a macromonomer (not assumed reactive).





The kMC model simulates the PLP experiment, including a total number of 100 pulses and an additional consideration of 10 seconds of reaction until the quenching agent is introduced in line with Marien *et al.* [34]. The log-MMDs are corrected for SEC broadening, in agreement with work by Buback *et al.* [103] (SEC broadening  $\sigma_{vb} = 0.042$ ). Also here it is recommended to have this SEC broadening determined at lower temperatures where the effects of the PMR and MCR are irrelevant.

A Monte Carlo control volume of  $10^{-14}$  L is considered to ensure convergence, considering previous work, optimizing the required simulation conditions to achieve the desired convergence in PLP simulations with many peaks and radical species [104, 105].

## Results and Discussion

In what follows, we first highlight that  $\gamma$  is likely not too close to 0 (e.g. not 0.01), by considering FRP simulations vs. typical experimental trends to then finetune that  $\gamma$  is likely also not too close to 1 (e.g. not 0.8), based on DFT calculations. We then propose a PLP-based method to determine  $\gamma$  with a first assessment of its value being 0.1 (325 K) based on literature data, to also formulate guidelines on the determination of acrylate specific rate coefficients in a roadmap format, including a focus on  $\gamma$ .

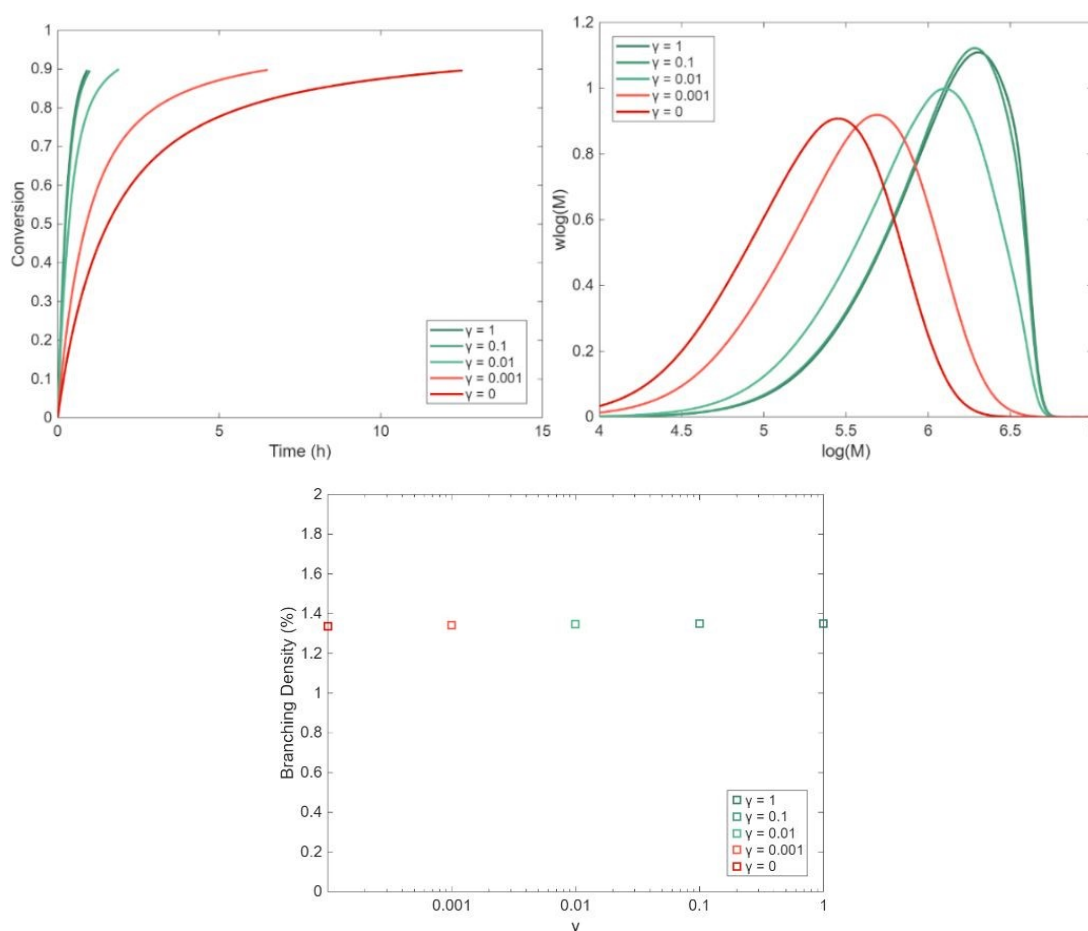


Figure 3. kMC simulation of FRP of *n*BuA initiated by AIBN, considering the parameters in Table 1 for different values of  $\gamma$  ( $\beta$  fixed at 1). (a) Monomer conversion vs time (h). (b) Log-MMD at a monomer conversion of 0.9 (c) Branching density at a monomer conversion of 0.9, defined as number of branches per monomer unit; 333 K and solvent fraction of 0.55;  $[AIBN]_0 = 3 \times 10^{-3}$  mol L $^{-1}$ . Green lines are realistic simulations so not too low  $\gamma$  values are expected (the currently accepted model is with  $\gamma = 1$  and gives specifically the expected experimental variation in polymerization rate). In the current work we assess  $\gamma$  as 0.1 at 325 K, consistent with the statement of not too low  $\gamma$  values.



### Sensitivity analysis under FRP conditions: likely a $\gamma$ value not too close to 0

View Article Online  
DOI: 10.1039/D5PY00343A

For  $\gamma=1$ , a PMR becomes an ECR and, hence, the original  $k$ MC model from our previous work results [18, 28, 34, 54]. For (solution) FRP conditions (333 K; AIBN as conventional initiator), this means variations for the monomer conversion, log-MMD, and MMD branching density at a monomer conversion of 0.9, as shown by the dark green lines/points in Figure 3.

Specifically, the monomer conversion profile time range (hour scale) and the branching density (1-3%) are in line with typical experimental variations [106, 107]. Note that Zhang et al. [108] e.g. show that a methyl acrylate (MA) conversion of 40% results in roughly half an hour. As  $n$ BuA propagates faster than MA, the dark green line in Figure 3a can be seen as at least qualitatively representative.

Moreover, Figure 3 presents the updates for the conversion profile, log-MMD and branching density in case  $\gamma$  values highly different from 1 are considered (not green but red lines). It follows that for the lowest  $\gamma$  value of zero, a completely different FRP is simulated. If  $\gamma$  is (very) low, implying an MCR-like propagation behavior for PMR, we obtain a very strong retardation, a very pronounced lowering of the chain length (although the branching density remains the same). These shifts are very unlikely seeing that common experimental FRP ranges [106, 107] are closer to the green lines/points ( $\gamma$  values larger than 0.01).

Furthermore, as illustrated in Figure S3 of the Supplementary Information, PMR backbiting has no impact on the key FRP properties, even if a very unrealistic high rate coefficient would be employed, implying a very high backbiting scaling factor  $\delta$  (Equation 3).

### DFT mechanistic insights: a $\gamma$ value likely not too close to 1

The DFT predicted rate coefficients are shown in Table 2 along with a previously published result via computational chemistry [69]. Our calculations reveal a higher activation energy and a lower pre-exponential parameter for PMR propagation, which could be related to the use of difference combination of basis set and model for the energetic correction. The difference between the literature published rate coefficient and our DFT calculation must be seen as qualitatively close. A comparison of exact numbers must be made with care because the energy correction method and the basis sets used are different, which can cause even orders of magnitude of difference. Moreover, the DFT predictions for ECR and MCR propagation are a good match with experimental values found out in literature [25, 72].

Table 2. Arrhenius parameters determined via DFT calculations for the different propagations involved in  $n$ BuA polymerization: ECR propagation, MCR propagation and PMR propagation. Literature values are also included for the latter

Reaction	Model/basis set	A $\text{L mol}^{-1} \text{s}^{-1}$	$E_a$ $\text{kJ mol}^{-1}$	$k$ (306K) $\text{L mol}^{-1} \text{s}^{-1}$	Ref.
ECR propagation	B3LYP/M06-2X//6-311+G(d,p)	$7.21 \times 10^6$	21.3	$1.7 \times 10^3$	<i>This work</i>
MCR propagation		$8.93 \times 10^5$	25.0	$4.9 \times 10^1$	<i>This work</i>
PMR propagation		$1.33 \times 10^6$	27.5	$2.7 \times 10^1$	<i>This work</i>
	B3LYP/MPWB1K//6-31G(d,p)	$1.17 \times 10^5$	20.2	$4.2 \times 10^1$	[69]

According to the computational chemistry results, the calculated PMR propagation rate coefficient is lower than the ECR propagation rate coefficient and more similar to the rate coefficient of the MCR propagation, hence,  $\gamma$  is likely not too close to 1. The FRP results of Figure 3 hinted at the opposite result so that overall intermediate  $\gamma$  values are too be expected. In any case, one should be careful by



simply plugging in values from computational chemistry in kinetic modeling studies. However, the current DFT study gives credibility to the existence of a PMR with different reactivity than an MCR and ECR.

### Further mechanistic insights: introducing a non-zero $\alpha$

The PMR species is likely capable of undergoing backbiting, similar to an ECR, although with some mechanistic differences. The ECR readily undergoes backbiting, due to the availability of a hydrogen atom for abstraction at a position that facilitates the formation of a stable 6-membered ring transition state. In contrast, the PMR has a more restricted polymer backbone, implying at first sight a  $\alpha$  lower than 1. However, as shown at the top of Figure 4, a PMR has available hydrogen atoms on both sides ("left" and "right") so that ignoring the previous effect a  $\alpha$  of 2 could be used.

The most likely reaction at low temperature conditions for the formed MCRs is further propagation with monomer, leading to the structures depicted in Figure 4 (bottom). The obtained products represent extra PMRs in terms of the radical placement in relation to the polymer backbone. However, now the structures have only one hydrogen atom available for an extra abstraction, as opposed to the two hydrogen atoms present in the initially formed PMR. This structural difference creates an issue with the previously introduced factor 2 used to account for the two backbiting possibilities (assuming a "lumped" PMR species). One can thus expect more a factor between 1 and 2 (still assuming similar mobilities between "left" and "right").

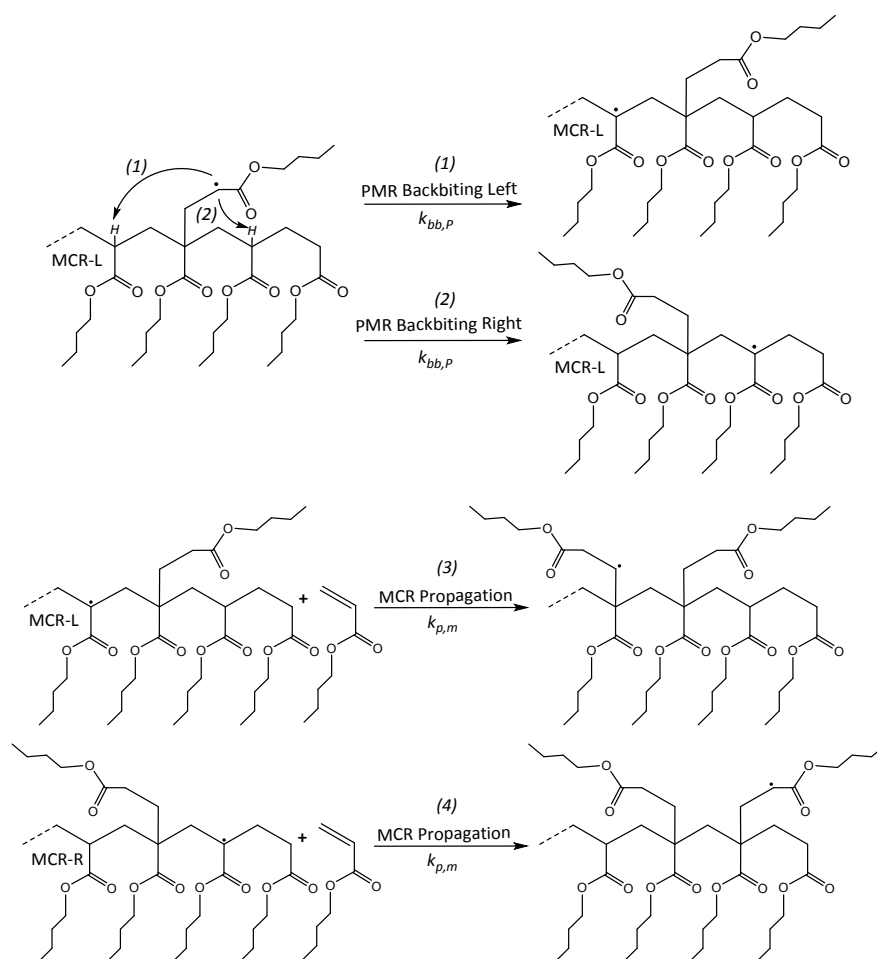


Figure 4. Top: Two backbiting reactions for PMR, for simplicity L(left) and R(right); Bottom: follow-up propagations.



Furthermore, the consideration of PMR backbiting (and further reactions) can result in a series of short branches next to each other. Such PMR-based mechanism increases the number of branches and additionally serves as a new mechanism for radical migration, similar to the consecutive six-ring hydrogen abstraction mechanism proposed by Kajiwaru [89-91]. This author stated that an actual mechanism is still ambiguous but there should be some stabilized mechanism to form helical structures of the model propagating radicals that have longer alkyl side groups. In this context, we hypothesize that the PMR will be part of the cause of said phenomena.

Note that short chain branching is a well-known structural property of vinyl polymers such as low density polyethylene [93]. However, the consideration of PMR backbiting in acrylate polymerization kinetics (and further reactions) can result in two types of different branches: the first, a series of sequential short branches next to each other separated only by one monomeric unit, the second, a branch with 3 or more units with little 1 unit protrusions. The first is a product of the PMR backbiting towards the "right" (see Figure 4) and then further propagation of the MCR/PMR. The second is a product of the PMR backbiting towards the "left" (see also Figure 4), resulting in a 3 unit branch with a small 1 unit protrusion. This last type of branch can be further extended with further PMR backbiting/MCR propagation sequences, extending the short branch by one unit and adding one small protrusion each time the cycle is repeated.

### Kinetic Monte Carlo PLP simulations to determine $\gamma$ and $\beta$

As highlighted in Equation (2),  $\gamma$  is a factor that adjusts the value of  $k_{p,p}$  linearly between its extreme theoretical values of either MCR or ECR propagation behavior ( $\gamma = 0$  and 1). In this subsection, we exploit PLP conditions to identify in the SEC trace sensitivities towards this  $\gamma$  factor. In a first phase, we deal with a frequency of 500 Hz, 100 laser pulses, a temperature of 306 K, and bulk conditions ( $\delta$  fixed to 1).

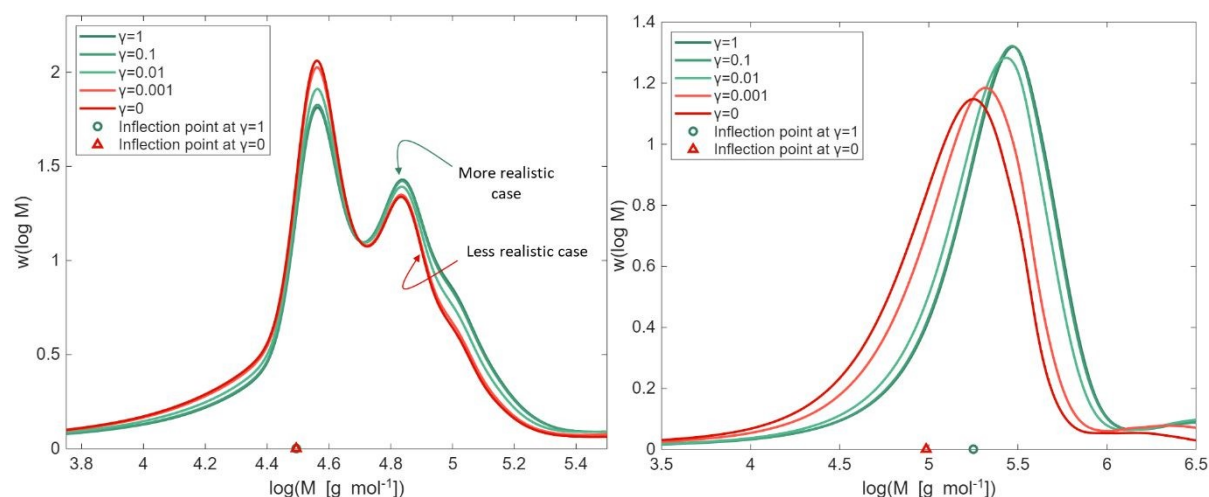


Figure 5. Left: kMC simulation of bulk PLP of *n*BuA at a laser pulse frequency of 500 Hz and 306 K, with a variation of  $\gamma$  (Equation (2));  $\gamma = 1$  implying  $k_{p,p} = k_{p,e}$  and  $\gamma = 0$  implying  $k_{p,p} = k_{p,m}$ ; Right similar plot but at a lower laser pulse frequency of 50 Hz; on the x-axis the identification of the first inflection points (left coinciding; right shift). Same coloring as in Figure 3, regarding expected behavior.

The results of the sensitivity analysis are shown in Figure 5 (left) and indicate sensitivity of the PLP-SEC peak heights with respect to a  $\gamma$  variation. With  $\gamma$  becoming smaller the average length of the polymer chains is reduced, because the PMR propagation resembles more the slower MCR propagation. This is consistent with the height of the first peak increasing (more shorter chains) and a reducing of the height of the second peak (less longer chains). The same trend is followed by the left



and right tail of the MMD. The front (left tail), dealing with shorter chains, is more evident in case  $\gamma$  is lower, and the (right) tail, dealing with longer chains becomes less stretched in case  $\gamma$  is lower.

It should be reminded that in Figure 5 (left) the  $\gamma$  values between 1 and 0.01 are the more realistic ones. As shown in Figure S4 of the Supplementary Information, still at 500 Hz but taking a temperature of 325 K, a reasonable experimental description of the PLP log-MMD is indeed obtained for a  $\gamma$  of 0.1. It should although be reminded that no other parameters have been tuned and here only one literature frequency is considered.

Notably, as shown by the triangles in Figure 5 (left), the  $\gamma$  variation at this studied high frequency of 500 Hz does not move the first inflection point of the MMD, which is used to determine  $k_{p,app}$  via Equation 1. This implies the overall consistency of the PLP-SEC method previously applied to determine  $k_{p,app}$  for acrylates [21-27]. The introduction of PMR as a different species does thus not invalidate previous research using a “simplified” model under the conditions of high frequency and low temperature. Complementary, the PMR as a new species can help to describe other features of the log-MMD and branching levels that were previously inaccessible.

The extra PMR species although changes the quasi-steady state based expression of the average propagation rate coefficient  $k_{p,av}$ , as highlighted in Section S5 of the Supplementary Information. Such average  $k_{p,av}$  is more representative for lower PLP frequencies and, hence, one can expect that at such frequencies the consistency of the inflection points no longer holds. Indeed, as shown in Figure 5 (right) at a lower frequency of 50 Hz, the inflection point of the MMD becomes sensitive to the value of  $\gamma$ . Lower values of  $\gamma$  shift the inflection point, due to the slower propagation with PMR, reducing  $k_{p,app}$  even by half if  $\gamma$  is very low. However, the likelihood of such a low value of  $\gamma$  is very low, reminding the results in Figure 3 for the FRP case.

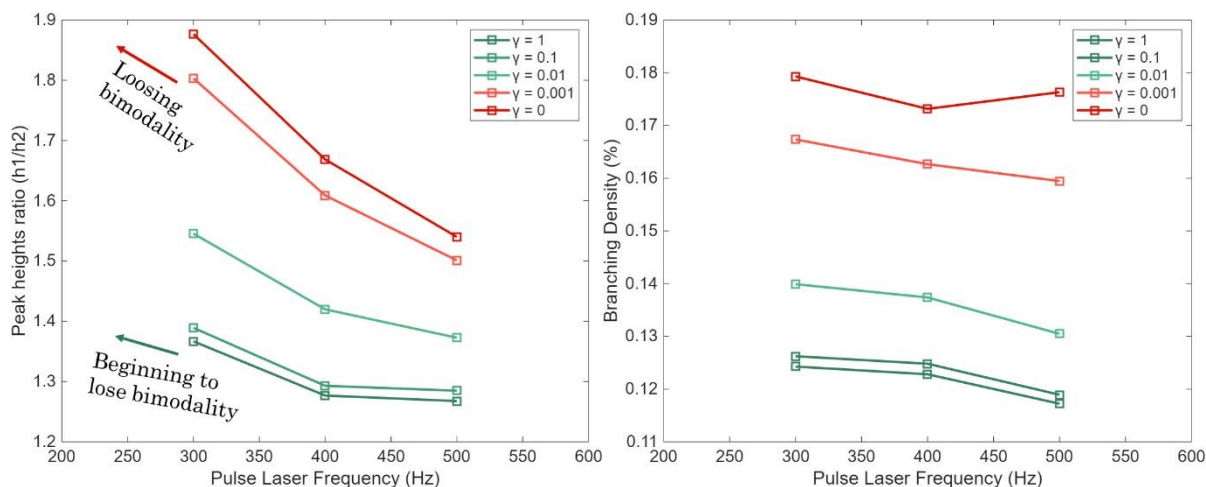


Figure 6. Left peak heights ratio at different values of  $\gamma$  (Equation 2) for PLP of *n*BuA at a laser pulse frequency of 500 Hz, at 306 K, and in bulk. The green lines represent the more likely values of  $\gamma$  within the 1-0.01 range (see Figure 1), and the red lines represent the more unlikely values of  $\gamma$  between 0.001-0. Right Corresponding branching densities.

The clear sensitivity of the peak heights at different frequencies in Figure 6 (left) is the basis to experimentally determine  $k_{p,p}$ , in future work at least if the frequencies are not too low (reminding Figure 5; right). Figure 6 (left) shows how the ratio of these peak heights (first vs second:  $h_1/h_2$ ) changes dependent on the pulse laser frequency as a function of  $\gamma$ . For a lower  $\gamma$ , the peak ratio increases and for a given  $\gamma$  a lower frequency has the same effect. For a lower  $\gamma$  (close to 0), a quasi-linear behavior is obtained with a lower frequency, and for a higher  $\gamma$  (close to 1) a clearer change in slope is obtained,





with more steepness for a lower frequency. Extra sensitivity is thus identified, as slope dependency would be seen or not, likely the former seeing the discussion of the FRP data in Figure 3.

As shown in Section S6 of the Supplementary Information, at lower frequencies, the bimodality of the SEC trace starts to disappear, consistent with Nikitin's work on backbiting [43]. The behavior of the double peaks is maintained roughly until a frequency of 300 Hz, with further lowering resulting in the loss of the bimodality behavior for  $\gamma$  values closer to 0.

It should also be admitted that the experimental determination of  $k_{p,p}$  by using the peak heights comes with several challenges, because these heights are also dependent on the termination kinetics, the pulse radical production and SEC broadening. Regarding termination kinetics, Section S1 of the Supplementary Information shows the negligible relevance of PMR termination towards the overall system. The pulse radical production in turn can cause differences in the peak heights as the amount of radicals produced change the rates of termination, causing macromolecules to move from one peak to the other. However, the amount of initiator radicals produced per pulse can be calculated using the Beer-Lambert law [92]: Equation 5. This equation allows to calculate the amount of radicals produced per pulse, and it is dependent on the properties of the laser and volume of the sample, which are not affected by the PMR kinetics. Additionally, the amount of radicals produced is affected by the quantum yield, which can also be related to the peak heights [28], although this parameter can be determined at a low temperature at which PMR/MCR are irrelevant. Hence, effectively decoupling the pulse radical production from the PMR kinetics is possible. Similarly, the band broadening function can be determined through independent experiments, especially for the acrylics esters whose propagation rates are high [109]. These independent calibration experiments use narrow standard polymers, integrity plots, or band broadening function deconvolution with known distributions [110, 111].

Figure S7 of the Supplementary Information shows the fractions of ECR, MCR and PMR as a function of temperature for different  $\gamma$  values at a frequency of 20 Hz, supported by EPR experimental data from Willemse et al. [56] considering only ECR and MCR fractions. In any case, the MCR radicals are dominant and PMR radicals are the least present in such way the trend from Willemse et al. [56] remains. Again the current work is thus in line with previously established trends.

Additional to the peak heights ratios, the branching density, which is accessible by NMR, shows sensitivity to the value of  $\gamma$ , as shown in Figure 6 (right). In case PMR propagation becomes slower (smaller  $\gamma$ ) the backbiting with PMR is more prominent, generating more one-unit branches besides each other in the polymer backbone, therefore, increasing the amount of branches as the value of  $\gamma$  decreases. Reminding the FRP results, a too low  $\gamma$  is although not expected, as otherwise the simulated values for the branching density are too high compared to typical measured branching densities of PLP-made acrylate polymers [112]. Hence, the results in Figure 6 (right) highlight that the branching density could serve as a property to determine the value of  $\gamma$  together with the peak heights ratio, although NMR analysis is more tedious. In any case,  $\gamma$  values between 0.1 and 1 seem to be undistinguishable.

For the  $\delta$  factor (Equation (3)), the sensitivity toward PLP parameters is much less. For example, as shown in Section S8 of the Supplementary information there is no sensitivity towards branching density, the inflection point nor the peak height, even at unlikely high  $\delta$  values ( $\gamma$  fixed at 1). However, by increasing the PLP solvent fraction, we can exploit the relation between the monomolecular backbiting reaction and the bimolecular propagation reaction. Figure 7 shows the effect of varying the solvent fraction for the branching density at different values of  $\delta$ . It follows that for a sufficiently diluted system a certain sensitivity is obtained, at least in case  $\delta$  would be above 1, which is





unfortunately in the more unrealistic zone of expected parameters. Hence, we expect that in many cases experimentally we would end up with a  $\delta$  set to 1.

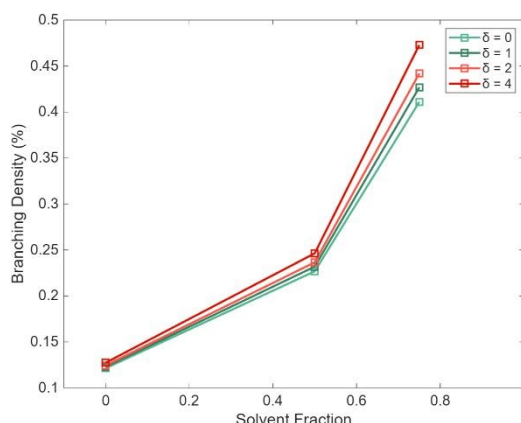


Figure 7. Branching density as a function of the solvent fraction for different  $\delta$  (Equation 3) values; PLP conditions: 500 Hz, at 306 K, fixing the value of  $\gamma$  to 1. In practice, one likely will end up setting  $\delta$  equal to 1.

#### Roadmap to determine $k_{p,e}$ , $k_{p,m}$ , $k_{p,p}$ , $k_{bb}$ , $k_{bb,p}$ , and $k_{\beta}$ .

Supported by previous work on  $k_{p,e}$  and  $k_{\beta}$  determination [18, 25] and the insights in the present work, we can formulate a step-wise PLP roadmap to come to reliable  $k_{p,e}$ ,  $k_{p,m}$ ,  $k_{p,p}$ ,  $k_{bb}$ ,  $k_{bb,p}$ , and  $k_{\beta}$  data, as illustrated in Figure 8.

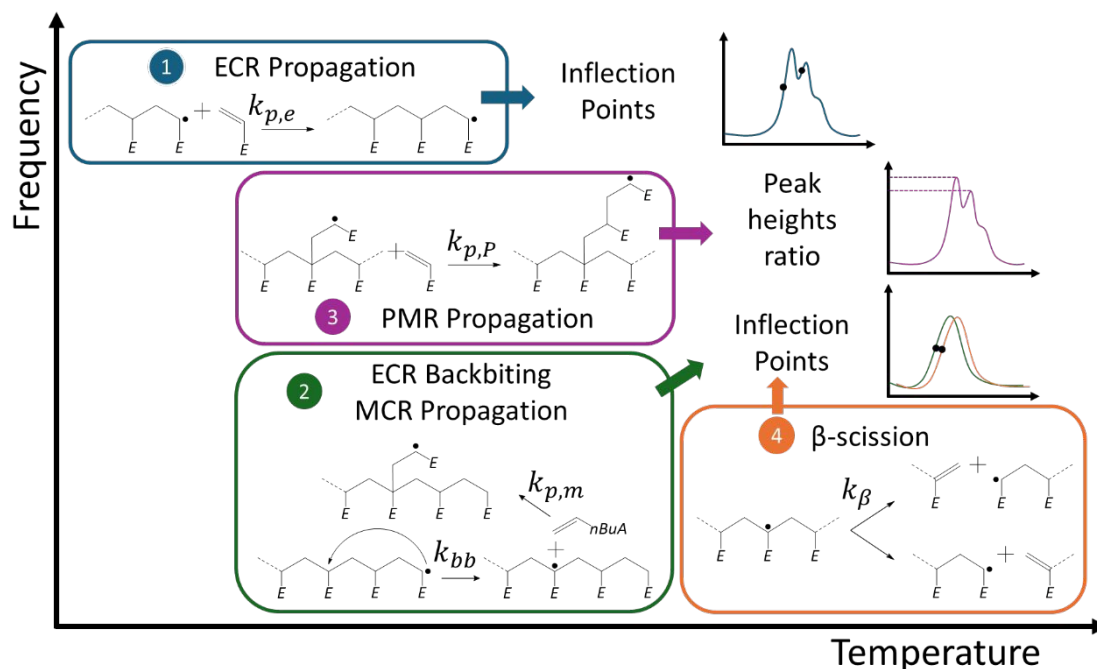


Figure 8. Roadmap to determine acrylate specific intrinsic rate coefficients, using PLP technique in combination with  $k$ MC simulations; not shown is the determination of  $k_{bb,p}$  for which branching densities can be used in Step 3, although likely  $k_{bb,p}$  is seen as  $k_{bb}$ .

For the PLP experiments, a distinction is made between frequency and temperature as well as four steps, in each step *e.g.* accounting for 3 temperatures to enable for the determination of Arrhenius parameters.



The first step deals with high frequencies and a low temperature to only allow for sensitivity toward the kinetic parameter with the highest rate coefficient and link to the primary ECR. Hence, Step 1 is devoted to the determination of  $k_{p,e}$ . In Step 2, the temperature is increased and the frequency lowered so that backbiting and tertiary propagation become kinetically relevant. Their joint estimation can be done to then check whether  $k_{p,p}$  (or better said  $\gamma$ ; Equation 2) is interfering or not. Likely this is not the case (so more  $\gamma$  away from 0) as verifiable by looking at the peak height ratios for different frequencies in Step 3. In parallel,  $k_{bb,p}$  (or  $\beta$ ; Equation 3) can be assessed but it can be expected that this parameter needs to be approximated by  $k_{bb}$  ( $\beta=1$ ). In Step 4, the temperature can be increased to allow for  $\beta$ -scission and, hence, the determination of  $k_{\beta}$  is within reach.

## Conclusions

By combining DFT and *k*MC simulations it is demonstrated that a MCR in *n*BuA radical polymerization is not directly transformed in a fully developed ECR. From a fundamental point of view, a propagated MCR (PMR) is better introduced to describe the kinetics in a more fundamental manner.

This PMR is kinetically defined by a transition propagation factor  $\gamma$  somewhat between 0 and 1, these borders implying MCR and ECR propagation behavior, respectively. *k*MC simulations under FRP conditions reveal that  $\gamma$  is likely not close to 0, and DFT calculations that  $\gamma$  is likely not close to 1. More importantly, the ratio of the peak heights under PLP conditions (at sufficiently high frequencies) is sensitive to  $\gamma$ , so that this experimentally accessible parameter can become relevant for  $\gamma$  determination in case the interfering model parameters, e.g. quantum yield, have been determined at low temperatures. Current literature PLP data at 500 Hz suggest a  $\gamma$  value of 0.1 at 325 K.

Furthermore, it is shown that PMR species can backbite, leading to a new migration mechanism as well as the formation of consecutive branches. Practically, the associated backbiting scaling factor  $\beta$  can be taken equal to 1, although it can be worthwhile to apply dilution in the bulk PLP region.

The current work puts forward an updated roadmap for the determination of acrylate specific rate coefficients, differentiating between the determination of  $k_{p,e}$ ,  $k_{p,m}$ ,  $k_{p,p}$ ,  $k_{bb}$ ,  $k_{bb,p}$ , and  $k_{\beta}$ .

## Acknowledgments

Y.W.M. acknowledges FWO Flanders for a postdoctoral grant (12B3Y24N).



## References

View Article Online  
DOI: 10.1039/D5PY00343A

1. Ballard, N. and J.M. Asua, *Radical polymerization of acrylic monomers: An overview*. Progress in Polymer Science, 2018. **79**: p. 40-60.
2. Passaglia, E., et al., *Some recent advances in polyolefin functionalization*. Polymer International, 2014. **63**(1): p. 12-21.
3. Gloor, P., et al., *Chemical modification of polyolefins by free radical mechanisms: a modelling and experimental study of simultaneous random scission, branching and crosslinking*. Polymer, 1994. **35**(5): p. 1012-1030.
4. Günaydin, H., et al., *Modeling the free radical polymerization of acrylates*. International Journal of Quantum Chemistry, 2005. **103**(2): p. 176-189.
5. Peck, A.N. and R.A. Hutchinson, *Secondary reactions in the high-temperature free radical polymerization of butyl acrylate*. Macromolecules, 2004. **37**(16): p. 5944-5951.
6. Guo, E., et al., *A cocktail strategy for enhancing flame retardance and water resistance of butyl acrylate coatings*. Materials Chemistry and Physics, 2021. **263**: p. 124367.
7. Elizalde, L.E., et al., *Synthesis of butyl acrylate–styrene–TMI latexes and their application as water-based coatings*. Journal of Coatings Technology and Research, 2020. **17**: p. 911-919.
8. Wu, J., et al., *Fabrication of water-resistance and durable antimicrobial adhesion polyurethane coating containing weakly amphiphilic poly (isobornyl acrylate) Side chains*. Progress in Organic Coatings, 2020. **147**: p. 105812.
9. Navaruckiene, A., et al., *Influence of Vanillin Acrylate-Based Resin Composition on Resin Photocuring Kinetics and Antimicrobial Properties of the Resulting Polymers*. Materials, 2021. **14**(3): p. 653.
10. Lebedevaite, M., V. Talacka, and J. Ostrauskaite, *High biorenewable content acrylate photocurable resins for DLP 3D printing*. Journal of Applied Polymer Science, 2021. **138**(16): p. 50233.
11. Pirman, T., et al., *Free radical copolymerization kinetics of bio-based dibutyl itaconate and n-butyl acrylate*. Chemical Engineering Journal, 2024. **499**: p. 156127.
12. Rubio, S., et al., *Tetrahydrofurfuryl methacrylate helps to produce biobased hydrophobic waterborne protective coatings by emulsion polymerization*. Progress in Organic Coatings, 2025. **203**: p. 109159.
13. Marien, Y.W., et al., *Exploiting the pulsed laser polymerization-size exclusion chromatography technique to retrieve kinetic parameters in radical polymerization: State-of-the-art and future challenges*, in *Advances in Chemical Engineering*. 2020, Elsevier. p. 59-95.
14. Willemse, R.X., et al., *PLP– ESR Monitoring of Midchain Radicals in n-Butyl Acrylate Polymerization*. Macromolecules, 2005. **38**(12): p. 5098-5103.
15. Mätzig, J., et al., *Kinetic Monte Carlo Simulations as a Tool for Unraveling the Impact of Solvent and Temperature on Polymer Topology for Self-Initiated Butyl Acrylate Radical Polymerizations at High Temperatures*. Macromolecular Theory and Simulations, 2023. **32**(4): p. 2300007.
16. Nikitin, A.N., et al., *Effect of Intramolecular Transfer to Polymer on Stationary Free-Radical Polymerization of Alkyl Acrylates, 5 – Consideration of Solution Polymerization up to High Temperatures*. Macromolecular Reaction Engineering, 2010. **4**(11-12): p. 691-706.
17. Edeleva, M., et al., *Impact of side reactions on molar mass distribution, unsaturation level and branching density in solution free radical polymerization of n-butyl acrylate under well-defined lab-scale reactor conditions*. Polymer Chemistry, 2021. **12**(14): p. 2095-2114.
18. Vir, A.B., et al., *From n-butyl acrylate Arrhenius parameters for backbiting and tertiary propagation to  $\beta$ -scission via stepwise pulsed laser polymerization*. Polymer Chemistry, 2019. **10**(30): p. 4116-4125.
19. Aleksandrov, A.P., et al., *Kinetics of laser-initiated polymerization and molecular-weight distribution of the resultant polymer*. Soviet Journal of Quantum Electronics, 1977. **7**(5): p. 547.



20. Olaj, O.F., I. Bitai, and G. Gleixner, *The laser flash-initiated polymerization as a tool of evaluating (individual) kinetic constants of free radical polymerization, 1. Outline of method and first results*. Die Makromolekulare Chemie, 1985. **186**(12): p. 2569-2580. View Article Online  
DOI: 10.1039/D5PY00343A
21. Buback, M., et al., *Critically evaluated rate coefficients for free-radical polymerization, 1. Propagation rate coefficient for styrene*. Macromolecular Chemistry and Physics, 1995. **196**(10): p. 3267-3280.
22. Beuermann, S., et al., *Critically evaluated rate coefficients for free-radical polymerization, 2.. Propagation rate coefficients for methyl methacrylate*. Macromolecular Chemistry and Physics, 1997. **198**(5): p. 1545-1560.
23. Beuermann, S., et al., *Critically evaluated rate coefficients for free-radical polymerization, 3. Propagation rate coefficients for alkyl methacrylates*. Macromolecular Chemistry and Physics, 2000. **201**(12): p. 1355-1364.
24. Beuermann, S., et al., *Critically Evaluated Rate Coefficients for Free-Radical Polymerization, 4*. Macromolecular Chemistry and Physics, 2003. **204**(10): p. 1338-1350.
25. Asua, J.M., et al., *Critically Evaluated Rate Coefficients for Free-Radical Polymerization, 5*. Macromolecular Chemistry and Physics, 2004. **205**(16): p. 2151-2160.
26. Beuermann, S., et al., *Critically evaluated rate coefficients for free-radical polymerization Part 6: Propagation rate coefficient of methacrylic acid in aqueous solution (IUPAC Technical Report)*. Pure and Applied Chemistry, 2007. **79**(8): p. 1463-1469.
27. Barner-Kowollik, C., et al., *Critically evaluated rate coefficients in radical polymerization – 7. Secondary-radical propagation rate coefficients for methyl acrylate in the bulk*. Polymer Chemistry, 2014. **5**(1): p. 204-212.
28. Marien, Y.W., et al., *Estimating the photodissociation quantum yield from PLP-SEC peak heights*. Polymer Chemistry, 2017. **8**(20): p. 3124-3128.
29. Haehnel, A.P., et al., *Solvent Effects on Acrylate  $k_p$  in Organic Media?—A Systematic PLP-SEC Study*. Macromolecular rapid communications, 2014. **35**(23): p. 2029-2037.
30. Barner-Kowollik, C., F. Günzler, and T. Junkers, *Pushing the limit: Pulsed laser polymerization of *n*-butyl acrylate at 500 Hz*. Macromolecules, 2008. **41**(23): p. 8971-8973.
31. Drawe, P. and M. Buback, *The PLP-SEC Method: Perspectives and Limitations*. Macromolecular Theory and Simulations, 2016. **25**(1): p. 74-84.
32. Sarnecki, J. and J. Schweer, *Conditions for the Determination of Precise and Accurate Free-Radical Propagation Rate Coefficients from Pulsed-Laser-Made Polymer*. Macromolecules, 1995. **28**(12): p. 4080-4088.
33. Nikitin, A.N., et al., *Detection of PLP structure for accurate determination of propagation rate coefficients over an enhanced range of PLP-SEC conditions*. Macromolecules, 2018. **52**(1): p. 55-71.
34. Marien, Y.W., et al., *Kinetic Monte Carlo modeling extracts information on chain initiation and termination from complete PLP-SEC traces*. Macromolecules, 2017. **50**(4): p. 1371-1385.
35. Desmet, G.B., et al., *Ab initio based kinetic Monte Carlo analysis to unravel the propagation kinetics in vinyl acetate pulsed laser polymerization*. Polymer Chemistry, 2017. **8**(46): p. 7143-7150.
36. Hutchinson, R.A., M.T. Aronson, and J.R. Richards, *Analysis of pulsed-laser-generated molecular weight distributions for the determination of propagation rate coefficients*. Macromolecules, 1993. **26**(24): p. 6410-6415.
37. Castignolles, P., *Transfer to Polymer and Long-Chain Branching in PLP-SEC of Acrylates*. Macromolecular rapid communications, 2009. **30**(23): p. 1995-2001.
38. Junkers, T. and C. Barner-Kowollik, *The role of mid-chain radicals in acrylate free radical polymerization: Branching and scission*. Journal of Polymer Science Part A: Polymer Chemistry, 2008. **46**(23): p. 7585-7605.



39. Plessis, C., et al., *Evidence of Branching in Poly (butyl acrylate) Produced in Pulsed-Laser Polymerization Experiments*. Macromolecular rapid communications, 2003. **24**(2): p. 173-177. View Article Online  
DOI: 10.1039/D5PY00343A
40. Plessis, C., et al., *A decrease in effective acrylate propagation rate constants caused by intramolecular chain transfer*. Macromolecules, 2000. **33**(1): p. 4-7.
41. Nikitin, A.N., et al., *Determination of Propagation Rate Coefficient of Acrylates by Pulsed-Laser Polymerization in the Presence of Intramolecular Chain Transfer to Polymer*. Macromolecular rapid communications, 2003. **24**(13): p. 778-782.
42. Buback, M., P. Hesse, and I. Lacík, *Propagation Rate Coefficient and Fraction of Mid-Chain Radicals for Acrylic Acid Polymerization in Aqueous Solution*. Macromolecular rapid communications, 2007. **28**(21): p. 2049-2054.
43. Nikitin, A.N., et al., *Determination of intramolecular chain transfer and midchain radical propagation rate coefficients for butyl acrylate by pulsed laser polymerization*. Macromolecules, 2007. **40**(24): p. 8631-8641.
44. Coote, M.L., et al., *Copolymerization Propagation Kinetics of Styrene and Methyl Methacrylate Revisited. 1. Pulsed Laser Polymerization Study*. Macromolecules, 1997. **30**(26): p. 8182-8190.
45. Hutchinson, R.A., et al., *A pulsed-laser study of penultimate copolymerization propagation kinetics for methyl methacrylate/n-butyl acrylate*. Industrial & engineering chemistry research, 1997. **36**(4): p. 1103-1113.
46. Marien, Y.W., et al., *Translating Simulated Chain Length and Molar Mass Distributions in Chain-Growth Polymerization for Experimental Comparison and Mechanistic Insight*. Macromolecular Theory and Simulations, 2021. **30**(3): p. 2170005.
47. De Smit, K., et al., *Roadmap for Monomer Conversion and Chain Length-Dependent Termination Reactivity Algorithms in Kinetic Monte Carlo Modeling of Bulk Radical Polymerization*. Industrial & Engineering Chemistry Research, 2020. **59**(52): p. 22422-22439.
48. Junkers, T. and C. Barner-Kowollik, *Optimum Reaction Conditions for the Synthesis of Macromonomers Via the High-Temperature Polymerization of Acrylates*. Macromolecular Theory and Simulations, 2009. **18**(7-8): p. 421-433.
49. Drache, M., et al., *Identification of  $\beta$  scission products from free radical polymerizations of butyl acrylate at high temperature*. Polymer Chemistry, 2019. **10**(15): p. 1956-1967.
50. Willemse, R.X.E. and A.M. van Herk, *Determination of Propagation Rate Coefficients of a Family of Acrylates with PLP-MALDI-ToF-MS*. Macromolecular Chemistry and Physics, 2010. **211**(5): p. 539-545.
51. Wenn, B. and T. Junkers, *Kilohertz Pulsed-Laser-Polymerization: Simultaneous Determination of Backbiting, Secondary, and Tertiary Radical Propagation Rate Coefficients for tert-Butyl Acrylate*. Macromolecular Rapid Communications, 2016. **37**(9): p. 781-787.
52. Wenn, B. and T. Junkers, *Kilohertz Pulsed-Laser-Polymerization: Simultaneous Determination of Backbiting, Secondary, and Tertiary Radical Propagation Rate Coefficients for tert-Butyl Acrylate*. Macromolecular rapid communications, 2016. **37**(9): p. 781-787.
53. Quintens, G. and T. Junkers, *Pulsed laser polymerization–size exclusion chromatography investigations into backbiting in ethylhexyl acrylate polymerization*. Polymer Chemistry, 2022. **13**(14): p. 2019-2025.
54. Marien, Y.W., et al., *An alternative method to estimate the bulk backbiting rate coefficient in acrylate radical polymerization*. Polymer Chemistry, 2016. **7**(42): p. 6521-6528.
55. Barth, J., et al., *EPR Analysis of n-Butyl Acrylate Radical Polymerization*. Macromolecular Rapid Communications, 2009. **30**(23): p. 1969-1974.
56. Willemse, R.X.E., et al., *PLP-ESR Monitoring of Midchain Radicals in n-Butyl Acrylate Polymerization*. Macromolecules, 2005. **38**(12): p. 5098-5103.





57. Barth, J. and M. Buback, *SP-PLP-EPR—A Novel Method for Detailed Studies into the Termination Kinetics of Radical Polymerization*. *Macromolecular Reaction Engineering*, 2010. **4**(5): p. 288-301.
58. Kattner, H., P. Drawe, and M. Buback, *Novel access to propagation rate coefficients of radical polymerization by the SP-PLP-EPR method*. *Macromolecular Chemistry and Physics*, 2015. **216**(16): p. 1737-1745.
59. Kattner, H. and M. Buback, *Propagation and chain-length-dependent termination rate coefficients deduced from a single SP-PLP-EPR experiment*. *Macromolecules*, 2016. **49**(10): p. 3716-3722.
60. Barth, J., *Radical polymerization kinetics in systems with transfer reactions studied by pulsed-laser-polymerization and online EPR-detection*. 2011.
61. Buback, M., et al., *Free-Radical Termination Kinetics Studied Using a Novel SP-PLP-ESR Technique*. *Macromolecular rapid communications*, 2004. **25**(10): p. 1004-1009.
62. Kattner, H. and M. Buback, *Chain-length-dependent termination of styrene bulk homopolymerization studied by SP-PLP-EPR*. *Macromolecules*, 2015. **48**(2): p. 309-315.
63. Barth, J. and M. Buback, *SP-PLP-EPR Investigations into the Chain-Length-Dependent Termination of Methyl Methacrylate Bulk Polymerization*. *Macromolecular rapid communications*, 2009. **30**(21): p. 1805-1811.
64. Kattner, H. and M. Buback, *Detailed Investigations into Radical Polymerization Kinetics by Highly Time-Resolved SP-PLP-EPR*. in *Macromolecular Symposia*. 2013. Wiley Online Library.
65. Barth, J., et al., *Chain-Length-Dependent Termination in Radical Polymerization of Acrylates*. *Macromolecular Chemistry and Physics*, 2011. **212**(13): p. 1366-1378.
66. Barth, J. and M. Buback, *SP-PLP-EPR Study into the termination kinetics of methacrylic acid radical polymerization in aqueous solution*. *Macromolecules*, 2011. **44**(6): p. 1292-1297.
67. Barth, J., W. Meiser, and M. Buback, *SP-PLP-EPR study into termination and transfer kinetics of non-ionized acrylic acid polymerized in aqueous solution*. *Macromolecules*, 2012. **45**(3): p. 1339-1345.
68. Soerensen, N., et al., *SP-PLP-EPR measurement of ATRP deactivation rate*. *Macromolecules*, 2012. **45**(9): p. 3797-3801.
69. Cuccato, D., et al., *A Density Functional Theory Study of Secondary Reactions in n-Butyl Acrylate Free Radical Polymerization*. *Macromolecular Theory and Simulations*, 2013. **22**(2): p. 127-135.
70. Lin, C.Y., et al., *Ab Initio Study of the Penultimate Effect for the ATRP Activation Step Using Propylene, Methyl Acrylate, and Methyl Methacrylate Monomers*. *Macromolecules*, 2007. **40**(16): p. 5985-5994.
71. Heuts, J.P.A. and G.T. Russell, *The nature of the chain-length dependence of the propagation rate coefficient and its effect on the kinetics of free-radical polymerization. 1. Small-molecule studies*. *European Polymer Journal*, 2006. **42**(1): p. 3-20.
72. Lugo, F.A., et al., *Secondary reactions during acrylate radical polymerization: Determining their rate coefficients*. *Polymer*, 2024. **300**: p. 126938.
73. Serse, F., M. Salvalaglio, and M. Pelucchi, *First Principles Assessment of Solvent Induced Cage Effects on Intramolecular Hydrogen Transfer in the Free Radical Polymerization of Acrylates*. *Physical Chemistry Chemical Physics*, 2024.
74. Lugo, F.A., et al., *Improved Approach for ab Initio Calculations of Rate Coefficients for Secondary Reactions in Acrylate Free-Radical Polymerization*. *Polymers*, 2024. **16**(7): p. 872.
75. Yu, X. and L.J. Broadbelt, *Kinetic Study of 1,5-Hydrogen Transfer Reactions of Methyl Acrylate and Butyl Acrylate Using Quantum Chemistry*. *Macromolecular Theory and Simulations*, 2012. **21**(7): p. 461-469.
76. Liu, S., et al., *Backbiting and  $\beta$ -scission reactions in free-radical polymerization of methyl acrylate*. *International Journal of Quantum Chemistry*, 2014. **114**(5): p. 345-360.





77. Moghadam, N., et al., *Theoretical Study of Intermolecular Chain Transfer to Polymer Reactions of Alkyl Acrylates*. Industrial & Engineering Chemistry Research, 2015. **54**(16): p. 4148-4165. View Article Online  
DOI: 10.1039/D5PY00343A
78. Mavrouidakis, E., D. Cuccato, and D. Moscatelli, *Quantum Mechanical Investigation on Bimolecular Hydrogen Abstractions in Butyl Acrylate-Based Free Radical Polymerization Processes*. The Journal of Physical Chemistry A, 2014. **118**(10): p. 1799-1806.
79. Cuccato, D., E. Mavrouidakis, and D. Moscatelli, *Quantum Chemistry Investigation of Secondary Reaction Kinetics in Acrylate-Based Copolymers*. The Journal of Physical Chemistry A, 2013. **117**(21): p. 4358-4366.
80. Frisch, M.J., et al., *Gaussian 16 Rev. C.01*. 2016: Wallingford, CT.
81. McQuarrie, D.A. and J.D. Simon, *Physical chemistry: a molecular approach*. Vol. 1. 1997: University science books Sausalito, CA.
82. Klamt, A., *Conductor-like Screening Model for Real Solvents: A New Approach to the Quantitative Calculation of Solvation Phenomena*. The Journal of Physical Chemistry, 1995. **99**(7): p. 2224-2235.
83. Klamt, A., et al., *Refinement and parametrization of COSMO-RS*. The Journal of Physical Chemistry A, 1998. **102**(26): p. 5074-5085.
84. Eckert, F. and A. Klamt, *Fast solvent screening via quantum chemistry: COSMO-RS approach*. AIChE Journal, 2002. **48**(2): p. 369-385.
85. COSMOtherm, R. (2019). "COSMOlogic GmbH & Co. KG, a Dassault Systèmes company."
86. Edeleva, M., et al., *Connecting Gas-Phase Computational Chemistry to Condensed Phase Kinetic Modeling: The State-of-the-Art*. Polymers, 2021. **13**(18): p. 3027.
87. Eyring, H., *The Activated Complex in Chemical Reactions*. The Journal of Chemical Physics, 1935. **3**(2): p. 107-115.
88. Eckart, C., *The penetration of a potential barrier by electrons*. Physical Review, 1930. **35**(11): p. 1303.
89. Kajiwar, A., *Studying the Fundamentals of Radical Polymerization Using ESR in Combination with Controlled Radical Polymerization Methods*, in *Radical Polymerization*. 2007. p. 50-59.
90. Kajiwar, A., *Electron Spin Resonance (ESR) Observation of Radical Migration Reactions in the Polymerization of Alkyl Acrylates*, in *Controlled/Living Radical Polymerization: Progress in ATRP*. 2009, American Chemical Society. p. 49-59.
91. Kajiwar, A., *A combination of Electron Spin Resonance spectroscopy/atom transfer radical polymerization (ESR/ATRP) techniques for fundamental investigation of radical polymerizations of (meth)acrylates*. Polymer, 2015. **72**: p. 253-263.
92. Ricci, R.W., M. Ditzler, and L.P. Nestor, *Discovering the Beer-Lambert Law*. Journal of Chemical Education, 1994. **71**(11): p. 983.
93. Odian, G., *Principles of Polymerization*. 2004: Wiley.
94. Castignolles, P., et al., *Pulsed Laser Polymerization of Alkyl Acrylates: Potential Effects of the Oxygen Presence and High Laser Power*. Macromolecular Chemistry and Physics, 2006. **207**(1): p. 81-89.
95. Haven, J.J., et al., *Efficiency assessment of single unit monomer insertion reactions for monomer sequence control: kinetic simulations and experimental observations*. Polymer Chemistry, 2015. **6**(31): p. 5752-5765.
96. Maeder, S. and R.G. Gilbert, *Measurement of Transfer Constant for Butyl Acrylate Free-Radical Polymerization*. Macromolecules, 1998. **31**(14): p. 4410-4418.
97. Barth, J., et al., *Termination and Transfer Kinetics of Butyl Acrylate Radical Polymerization Studied via SP-PLP-EPR*. Macromolecules, 2010. **43**(9): p. 4023-4031.
98. Lewis, F.M. and M.S. Matheson, *Decomposition of Aliphatic Azo Compounds*. Journal of the American Chemical Society, 1949. **71**(2): p. 747-748.
99. Walz, R., B. Bömer, and W. Heitz, *Monomeric and polymeric azoinitiators*. Die Makromolekulare Chemie, 1977. **178**(9): p. 2527-2534.



100. Derboven, P., et al., *The Long and the Short of Radical Polymerization*. *Macromolecules*, 2015. **48**(3): p. 492-501. View Article Online  
DOI: 10.1039/D5PY00343A
101. Tripathi, A.K., J.G. Tsavalas, and D.C. Sundberg, *Monte Carlo Simulations of Free Radical Polymerizations with Divinyl Cross-Linker: Pre- and Postgel Simulations of Reaction Kinetics and Molecular Structure*. *Macromolecules*, 2015. **48**(1): p. 184-197.
102. Hamzehlou, S., et al., *Analyzing the discrepancies in the activation energies of the backbiting and  $\beta$ -scission reactions in the radical polymerization of n-butyl acrylate*. *Polymer Chemistry*, 2016. **7**(11): p. 2069-2077.
103. Buback, M., M. Busch, and R.A. Lämmel, *Modeling of molecular weight distribution in pulsed laser free-radical homopolymerizations*. *Macromolecular theory and simulations*, 1996. **5**(5): p. 845-861.
104. Trigilio, A.D., et al., *A Signal-To-Noise-Ratio-Based Automated Algorithm to accelerate Kinetic Monte Carlo Convergence in Basic Polymerizations*. *Advanced Theory and Simulations*, 2024. **7**(2): p. 2300637.
105. Trigilio, A.D., et al., *Toward an Automated Convergence Tool for Kinetic Monte Carlo Simulation of Conversion, Distributions, and Their Averages in Non-dispersed Phase Linear Chain-Growth Polymerization*. *Industrial & Engineering Chemistry Research*, 2023. **62**(6): p. 2583-2593.
106. Ahmad, N.M., F. Heatley, and P.A. Lovell, *Chain Transfer to Polymer in Free-Radical Solution Polymerization of n-Butyl Acrylate Studied by NMR Spectroscopy*. *Macromolecules*, 1998. **31**(9): p. 2822-2827.
107. Ahmad, N.M., et al., *Chain Transfer to Polymer and Branching in Controlled Radical Polymerizations of n-Butyl Acrylate*. *Macromolecular Rapid Communications*, 2009. **30**(23): p. 2002-2021.
108. Zhang, Z., et al., *Free radical polymerization of acrylates bearing acetylene for preparation of clickable polymers*. *Polymer*, 2021. **228**: p. 123906.
109. Buback, M., M. Busch, and R.A. Lämmel, *Modeling of molecular weight distribution in pulsed laser free-radical homopolymerizations*. *Macromolecular Theory and Simulations*, 1996. **5**(5): p. 845-861.
110. *Band Broadening Function in Size Exclusion Chromatography of Polymers*. *Chemistry International -- Newsmagazine for IUPAC*, 2008. **30**(2): p. 27-27.
111. Goyon, A., D. Guilleme, and S. Fekete, *The importance of system band broadening in modern size exclusion chromatography*. *Journal of pharmaceutical and biomedical analysis*, 2017. **135**: p. 50-60.
112. Arzamendi, G. and J.R. Leiza, *Molecular Weight Distribution (Soluble and Insoluble Fraction) in Emulsion Polymerization of Acrylate Monomers by Monte Carlo Simulations*. *Industrial & Engineering Chemistry Research*, 2008. **47**(16): p. 5934-5947.



All key data is reported in the manuscript and the Supplementary Information.

