

Cite this: *Chem. Sci.*, 2021, 12, 9742

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Coexistence of magnetic and electric orderings in a divalent $\text{Cr}^{2+}$ -based multiaxial molecular ferroelectric†

Yong Ai,<sup>‡a</sup> Rong Sun,<sup>‡b</sup> Yu-Ling Zeng,<sup>a</sup> Jun-Chao Liu,<sup>a</sup> Yuan-Yuan Tang,<sup>a</sup> Bing-Wu Wang,<sup>b</sup> Zhe-Ming Wang,<sup>b</sup> Song Gao<sup>\*,b</sup> and Ren-Gen Xiong<sup>\*,a</sup>

Multiferroic materials have attracted great interest because of their underlying new science and promising applications in data storage and mutual control devices. However, they are still very rare and highly imperative to be developed. Here, we report an organic–inorganic hybrid perovskite trimethylchloromethylammonium chromium chloride (TMCM– $\text{CrCl}_3$ ), showing the coexistence of magnetic and electric orderings. It displays a paraelectric–ferroelectric phase transition at 397 K with an Aizu notation of  $6/m\text{Fm}$ , and spin-canted antiferromagnetic ordering with a Néel temperature of 4.8 K. The ferroelectricity originates from the orientational ordering of TMCM cations, and the magnetism is from the  $[\text{CrCl}_3]^-$  framework. Remarkably, TMCM– $\text{CrCl}_3$  is the first experimentally confirmed divalent  $\text{Cr}^{2+}$ -based multiferroic material as far as we know. A new category of hybrid multiferroic materials is pointed out in this work, and more  $\text{Cr}^{2+}$ -based multiferroic materials will be expectedly developed in the future.

Received 3rd April 2021  
Accepted 14th June 2021

DOI: 10.1039/d1sc01871j

rsc.li/chemical-science

## Introduction

Ferroelectric materials, which involve a variety of substances containing inorganic ceramics, organic compounds, and organic–inorganic hybrids, have long attracted enormous attention for their technological applications in transducers, capacitors, sensors, *etc.*<sup>1–6</sup> By comparison, multiferroic materials simultaneously possess at least two ferroic orders in a single phase. The coexistence of magnetic order and ferroelectricity is especially attractive for their underlying scientific significance and promising applications in multistate data storage and signal process.<sup>7–9</sup> However, multiferroics have been very rare to date, and the most studied ones are inorganic transition-metal oxides,<sup>10–13</sup> such as  $\text{BiFeO}_3$ ,<sup>14</sup>  $\text{BiMnO}_3$ ,<sup>15</sup>  $\text{RMnO}_3$  ( $\text{R}$  = rare earth elements),<sup>16</sup> and  $\text{TbMn}_2\text{O}_5$ ,<sup>17</sup> because the mutual exclusion between ferroelectricity and magnetism makes this combination so challenging to achieve. In general, magnetism usually results from the ordered spins of electrons in the partially filled d orbitals of transition metals, while

ferroelectricity requires residual polarization from a stable off-centred ion with empty d shells.<sup>18–21</sup> To address this contradiction, the research has been extended to organic–inorganic hybrid frameworks in an attempt to open up a new avenue to multiferroic behaviour.

In organic–inorganic hybrid ferroelectrics, the polar electric ordering generally originates from the ordering alignments associated with organic components.<sup>22–24</sup> Beyond conventional inorganic materials, hybrid ones that merge the benefits of both organic molecules and inorganic skeletons are promising candidates for various multifunctional materials.<sup>25–28</sup> Most of the discovered and theoretically predicted hybrid multiferroics are a series of three-dimensional metal–organic frameworks, represented by  $[\text{ammonium}][\text{M}(\text{HCOO})_3]$ , where  $\text{M}^{2+}$  is a transition-metal ion such as  $\text{Cu}^{2+}$ ,  $\text{Mn}^{2+}$ ,  $\text{Fe}^{2+}$  and  $\text{Ni}^{2+}$ .<sup>29–33</sup> The magnetism and ferroelectricity in these compounds have different origins: the magnetism derives from the  $[\text{M}(\text{HCOO})_3]^-$  framework while the ferroelectric order is attributed to the order–disorder transition associated with organic components. However, currently reported organic–inorganic hybrid multiferroics are even rarer than inorganic oxides, and the material diversity is greatly restricted despite other new sporadic cases being reported.<sup>32–42</sup> In this context, it is highly imperative to develop new types of hybrid multiferroics. In an attempt to open up a new avenue of multiferroic materials, we have investigated compounds of Cr in its (unusual) divalent state. Stroppa *et al.* had theoretically predicted that a  $\text{Cr}^{2+}$ -based perovskite  $[\text{C}(\text{NH}_2)_3][\text{Cr}(\text{HCOO})_3]$  might be a new multiferroic, while it had not been successfully synthesized.<sup>43</sup>

<sup>a</sup>Ordered Matter Science Research Center, Nanchang University, Nanchang 330031, P. R. China. E-mail: xiongrg@seu.edu.cn

<sup>b</sup>Beijing National Laboratory for Molecular Sciences, State Key Laboratory of Rare Earth Materials Chemistry and Applications, College of Chemistry and Molecular Engineering, Peking University, Beijing 100871, P. R. China. E-mail: gaosong@pku.edu.cn

† Electronic supplementary information (ESI) available. CCDC 2054834 and 2054835. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d1sc01871j

‡ These authors contributed equally to this work.

Based on the work on targeted design strategies for molecular ferroelectrics,<sup>44</sup> herein, we successfully design a new organic–inorganic hybrid multiferroic, trimethylchloromethylammonium chromium chloride (TMCM–CrCl<sub>3</sub>), which simultaneously shows excellent ferroelectricity and antiferromagnetism. Its paraelectric–ferroelectric transition at 397 K is related to the disorder–order transition of TMCM cations, and the magnetism is from the [CrCl<sub>3</sub>]<sup>−</sup> framework. Notably, the observed C–Cl⋯Cl–Cr interactions between organic and inorganic components in TMCM–CrCl<sub>3</sub> play an important role in ensuring and stabilizing its polar organic–inorganic hybrid structure and ferroelectricity. To our knowledge, TMCM–CrCl<sub>3</sub> is the first experimentally confirmed Cr<sup>2+</sup>-based multiferroic material, and also is the first Cr<sup>2+</sup>-based organic–inorganic hybrid perovskite ferroelectric material. This work expectedly sheds light on the design of new multiferroic materials and inspires further exploration of the connection between the structure and properties.

## Results and discussion

The crystal of TMCM–CrCl<sub>3</sub> adopts a BaNiO<sub>3</sub>-like hexagonal perovskite structure, where infinite linear chains of face-sharing CrCl<sub>6</sub> octahedra are separated by the TMCM cations (Fig. 1 and ESI, Fig. S1†), analogous to several other ABX<sub>3</sub>-type hybrid perovskites. In a low-temperature phase (LTP) below a Curie temperature (*T*<sub>c</sub>) of 397 K, TMCM–CrCl<sub>3</sub> crystallizes in the monoclinic polar space group *P*<sub>c</sub> (ESI, Table S1†). The structure in LTP was refined as an ordered state with distorted [CrCl<sub>6</sub>] octahedra. Fig. 1 depicts the structure of 3d<sup>4</sup> [CrCl<sub>3</sub>]<sup>−</sup> ions, which is the source of magnetism in the lattice. Structurally, TMCM cations adopt a manner of head-to-tail alignment along the *a*-axis, and the directions of C–Cl bonds are skewed toward the *c*-axis (Fig. 1a). The short intermolecular Cl⋯Cl contacts (3.236 and 3.243 Å) lead to the formation of C–Cl⋯Cl–Cr halogen bonds (bond angles of 177.07° and 173.79°) (ESI, Fig. S2†). Besides the size and weight of the molecule, the relatively strong halogen bonds play an important role in the cationic alignment, crystal symmetry and the potential energy barrier of molecular motion. These attributes make TMCM cations arrange in an orderly manner, resulting in a non-centrosymmetric structure and consequential spontaneous polarization. Additionally, because the [CrCl<sub>3</sub>]<sup>−</sup> chains are separated by TMCM cations, intra-chain Cr⋯Cr distances are 3.309 Å and 3.335 Å, while the shortest inter-chain Cr⋯Cr distance reaches 9.069 Å (ESI, Fig. S3a†), which will lead to strong intra-chain Cr⋯Cr magnetic couplings and weak inter-chain Cr⋯Cr ones.

In the high-temperature phase (HTP, above *T*<sub>c</sub>), the crystal structure of TMCM–CrCl<sub>3</sub> transforms to locating in the hexagonal centrosymmetric space group *P*6<sub>3</sub>/*m* (ESI, Table S1†). The configuration of [CrCl<sub>3</sub>]<sup>−</sup> chains is similar to that of LTP, while the CrCl<sub>6</sub> octahedra become more regular (Fig. 1b), and the shortest intra/inter-chain Cr⋯Cr distances are 3.327 Å and 9.406 Å, respectively (ESI, Fig. S3b†). For the TMCM cation, its symmetry site changes from a general position in LTP to a special one of  $\bar{6}/m$  (Fig. 1c and d), and thus the cations were modeled as 6-fold orientational disorder to satisfy the crystallographic symmetries. In HTP, the head-to-head and tail-to-tail

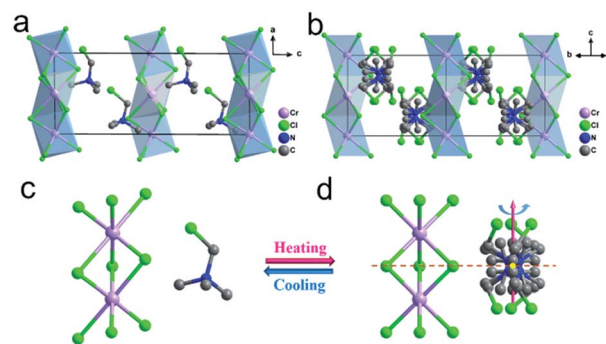


Fig. 1 Crystal structures of TMCM–CrCl<sub>3</sub>. Packing view of a structure in (a) LTP and (b) HTP. (c) Structural unit in LTP, showing a distorted [CrCl<sub>6</sub>] octahedron and ordered TMCM cations. (d) Structural unit in HTP, showing a regular [CrCl<sub>6</sub>] octahedron and orientationally disordered TMCM cations. The brown line represents the mirror plane perpendicular to the *c*-axis. The pink arrow indicates the 6-fold rotoinversion axis. The yellow point represents the inversion center. H atoms were omitted for clarity.

alignments of TMCM cations lead to a centrosymmetric structure. Therefore, the paraelectric–ferroelectric phase transition mechanism can be attributed to the disorder–order transition of TMCM cations. The ferroelectricity is induced by the orientational ordering of TMCM cations, and the magnetism results from the transition metal 3d<sup>4</sup> CrII ions.

The phase transition behavior of TMCM–CrCl<sub>3</sub> was directly detected by differential scanning calorimetry (DSC) measurements. From DSC curves (Fig. 2a), two pairs of successive thermal anomalies are observed at 381/371 K and 397/386 K in the heating/cooling runs, both of which are too close together to be separated, and thus can be considered as only one phase transition at about 397 K. Known from curves, the enthalpy change  $\Delta H$  of TMCM–CrCl<sub>3</sub> is about 4.2 J g<sup>−1</sup>. According to the

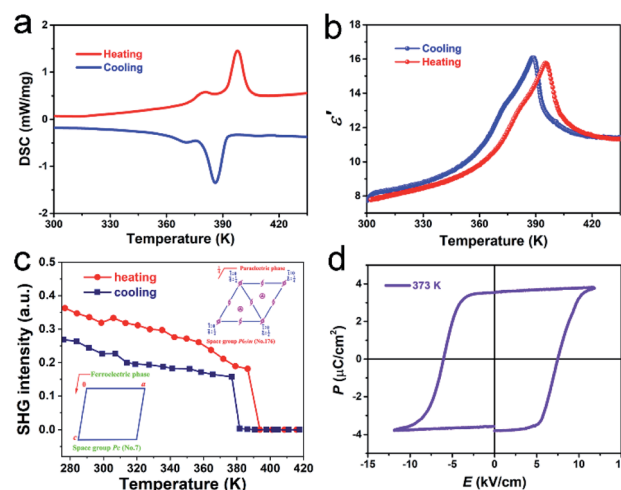


Fig. 2 Physical properties of TMCM–CrCl<sub>3</sub>. (a) DSC curves in heating and cooling runs. (b) The real part ( $\epsilon'$ ) of dielectric permittivity as a function of temperature. (c) Temperature-dependent SHG response in the heating and cooling runs. (d) *P*–*E* hysteresis loop measured along the polar axis of LTP at 373 K and 50 Hz.



formula  $\Delta S = \Delta H/T$ , the entropy change  $\Delta S$  of the phase transition is calculated to be  $5.6 \text{ J mol}^{-1} \text{ K}^{-1}$ . The calculated  $N$  value is 1.97 around  $T_c$  based on the Boltzmann equation  $\Delta S = R \ln(N)$ , where  $R$  represents the gas constant and  $N$  stands for the possible orientation number. Such a large  $N$  value reveals that the compound has a reversible transition between ordered and disordered states. Meanwhile, the real part ( $\epsilon'$ ) of the dielectric permittivity of TMCM- $\text{CrCl}_3$  shows corresponding dielectric anomalies (Fig. 2b), consistent with the DSC result and further confirming the existence of a phase transition at a  $T_c$  of 397 K. We also performed the second harmonic generation (SHG) experiment to investigate the phase transition behaviour. As shown in Fig. 2c, TMCM- $\text{CrCl}_3$  displays a clear SHG at room temperature. In the heating and cooling runs, the detectable SHG response below  $T_c$  demonstrates the polar space group  $P_c$  in the ferroelectric phase. Near  $T_c$ , the sudden vanishing of the SHG response means that it enters into an SHG non-active state, in good agreement with the centrosymmetric  $6/m$  point group in the paraelectric phase. In this case, symmetry breaking occurs with an Aizu notation of  $6/mFm$ ,<sup>45</sup> accompanied by a decrease in macroscopic symmetry elements from 12 ( $E$ ,  $2C_6$ ,  $2C_3$ ,  $C_2$ ,  $i$ ,  $2S_3$ ,  $2S_6$ , and  $\sigma_h$ ) in the paraelectric phase to 2 ( $E$  and  $\sigma_h$ ) in the ferroelectric phase. Accordingly, TMCM- $\text{CrCl}_3$  is a multiaxial ferroelectric with 6 equivalent polarization directions, corresponding to 3 ferroelectric axes.

To examine the ferroelectricity of TMCM- $\text{CrCl}_3$ , we measured the polarization–electric field ( $P$ – $E$ ) hysteresis loop by using the Sawyer–Tower method at 298 K (Fig. 2d). A typical well-shaped  $P$ – $E$  hysteresis loop was recorded, directly confirming the ferroelectricity of TMCM- $\text{CrCl}_3$ . The measured saturated polarization ( $P_s$ ) and remnant polarization ( $P_r$ ) are almost equal, about  $3.6 \mu\text{C cm}^{-2}$ , compared to that of TMCM- $\text{CdBr}_3$  ( $3.5 \mu\text{C cm}^{-2}$ ),<sup>46</sup> and larger than those of other organic–inorganic hybrid multiferroics such as  $(\text{NH}_4)_3\text{CrO}_8$  ( $0.25 \mu\text{C cm}^{-2}$ ),<sup>35</sup> triethylmethylammonium tetrabromoferrate(III) ( $0.9 \mu\text{C cm}^{-2}$ ),<sup>34</sup> and  $[\text{NH}_4][\text{M}(\text{HCOO})_3]$  ( $\text{M} = \text{Mn, Fe, Co, Ni, and Zn}$ ) ( $0.97$ – $2.2 \mu\text{C cm}^{-2}$ ).<sup>31</sup>

In order to gain deep insight into the ferroelectric polarization, density functional theory (DFT) calculation was carried out to evaluate the origin of polarization.<sup>43,47</sup> According to the modern theory of polarization,<sup>48,49</sup> the necessity of constructing a polarization change path lies in selecting polarization quantum properly to avoid the wrong estimation of the polarization value. A dynamic path between ferroelectric and reference states is constructed based on the crystal structure obtained from single crystal X-ray diffraction, while the other states are obtained from the matrix transformation of the coordinates considering both the rotation of the TMCM cations and displacement of the anionic  $\text{CrCl}_3$  framework. The variation of polarization as a function of the dynamic path is shown in ESI, Fig. S4,<sup>†</sup> from which the ferroelectric polarization with  $4.82 \mu\text{C cm}^{-2}$  along the  $a$ -axis and  $3.37 \mu\text{C cm}^{-2}$  along the  $c$ -axis can be extracted from the ferroelectric configurations ( $\lambda = 1$ ). Meanwhile the polarization along the  $b$ -axis is zero, which is in good accordance with the symmetry of the space group  $P_c$ . Along with the constructed path ( $0 < \lambda < 1$ ), the polarization

value changes smoothly, and turns to zero at  $\lambda = 0$ , which indicates a reference phase with zero polarization.

The structure of TMCM- $\text{CrCl}_3$  consists of  $[\text{CrCl}_3]^-$  anionic chains and TMCM cations. The  $[\text{CrCl}_3]^-$  chain is made of 4 + 2 elongated  $[\text{CrCl}_6]$  octahedra by face-sharing, and the chains are separated by the TMCM cations (detailed molecular geometries have been discussed above, such as intra/inter-chain  $\text{Cr}\cdots\text{Cr}$  distances). Therefore, it is expected that the intra-chain  $\text{Cr}\cdots\text{Cr}$  magnetic couplings will be strong, and the inter-chain  $\text{Cr}\cdots\text{Cr}$  ones will be weak. Indeed, the material is a spin-canted anti-ferromagnetic with strong intra-chain antiferromagnetic coupling. Under a 100 Oe field, the  $\chi$  vs.  $T$  data showed broad maxima around 70 K ( $=T(\chi_{\text{max}})$ ) caused by strong intra-chain antiferromagnetic coupling (Fig. 3a). Below 15 K the trace rose up quickly. On cooling, the  $\chi T$  values continuously went down from  $1.94 \text{ cm}^3 \text{ K mol}^{-1}$  at 300 K to  $0.13 \text{ cm}^3 \text{ K mol}^{-1}$  around 7 K, and then rose to a maximum of  $0.37 \text{ cm}^3 \text{ K mol}^{-1}$  at 4.0 K, and finally reached  $0.25 \text{ cm}^3 \text{ K mol}^{-1}$  at 2 K. In higher fields of 2 and 10 kOe, the  $\chi T$  rises below 7 K were suppressed. This indicated the occurrence of spin-canted antiferromagnetism or weak ferromagnetism in the low-temperature region. Fitting the high-temperature susceptibility data (above 200 K and under 100 Oe) by the Curie–Weiss law (ESI, Fig. S5<sup>†</sup>), the Curie and Weiss constants could be obtained,  $C = 3.30 \text{ cm}^3 \text{ K mol}^{-1}$  and  $\theta = -209 \text{ K}$ , respectively. The  $C$  value is expected for octahedral  $\text{CrII}$  with  $S = 2$ ,<sup>50</sup> and the large, negative  $\theta$  value indicates strong intra-chain  $\text{Cr}\cdots\text{Cr}$  antiferromagnetic couplings. In fact, the significantly low  $\chi T$  value of  $1.94 \text{ cm}^3 \text{ K mol}^{-1}$  (compared with  $3.00 \text{ cm}^3 \text{ K mol}^{-1}$  for spin-only, un-coupled spins of  $S = 2$ ) at room temperature is due to such strong intra-chain antiferromagnetic couplings. From Fig. 3b–d, the zero-field-cooling and field-cooling (ZFC/FC, with small magnetizations of a few  $\text{cm}^3 \text{ G mol}^{-1}$ ) runs, the isothermal magnetizations (with small  $H_C = 110 \text{ Oe}$ ,  $M_R = 0.00133N_\beta$  and  $M_{50\text{kOe}} = 0.191N_\beta$ ) and the frequency-independent peaks in ac susceptibility data (ESI,

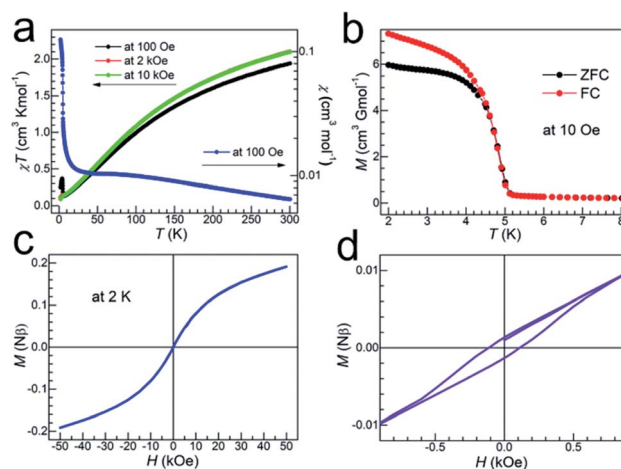


Fig. 3 Magnetic properties of TMCM- $\text{CrCl}_3$ . (a) Temperature dependence of the magnetic susceptibility ( $\chi T$ ). (b) Zero-field-cooling and field-cooling magnetization ( $M$ ) under 10 Oe fields. (c) Field-dependent isothermal magnetization ( $M$ ) at 2 K. (d) The zoomed views of magnetic hysteresis from (c).





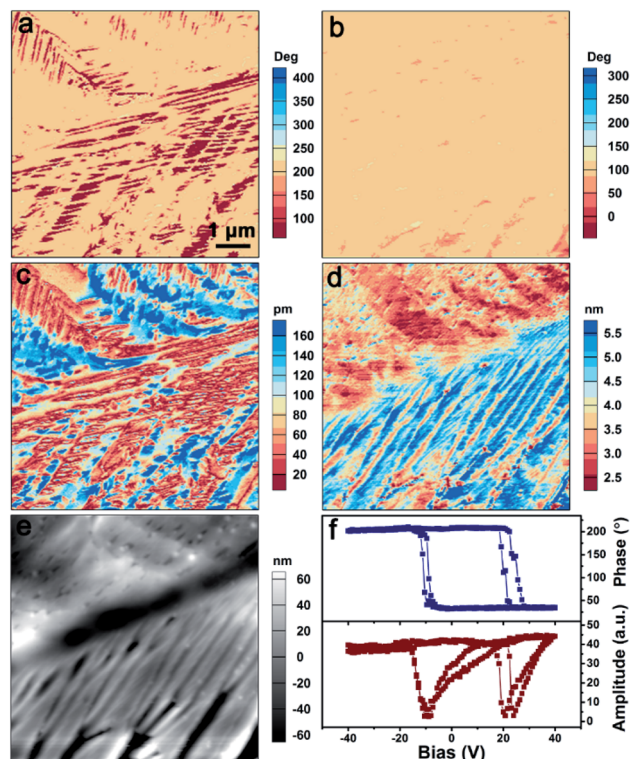


Fig. 4 Vertical PFM phase (a) and amplitude (c) images, lateral PFM phase (b) and amplitude (d) images, and topography (e) image of the thin film of TMCM-CrCl<sub>3</sub>. (f) Vertical PFM phase and amplitude signals versus the tip voltage for a selected point, displaying local piezoelectric hysteresis loops.

Fig. S6†) all confirmed the spin-canted antiferromagnetic orderings in the low temperature region. The Néel temperature ( $T_N$ ) is 4.8 K, determined by ZFC/FC and ac measurements. Finally, the intra-chain Cr<sup>II</sup>...Cr<sup>II</sup> antiferromagnetic coupling  $J$  could be estimated to be  $J/k \approx 10$  K, by using the equation of  $kT(\chi_{\max})/|J| \approx 7.1$ ,<sup>51</sup> assuming that the chain is of Heisenberg type with  $S = 2$ .

Next, piezoresponse force microscopy (PFM) measurements were performed as they represent the most well-known technique for elucidating the ferroelectric properties at the nanoscale. Fig. 4a–e show the PFM mapping of the as-grown TMCM-CrCl<sub>3</sub> thin film, including the vertical PFM phase (Fig. 4a) and amplitude (Fig. 4c), lateral PFM phase (Fig. 4b) and amplitude (Fig. 4d) images and the corresponding topographic image (Fig. 4e). It reveals that domains with different polarization directions exist in TMCM-CrCl<sub>3</sub>. These polarizations have opposite out-of-plane directions but the same in-plane direction, as presented by the vertical and lateral PFM phase images. Thus, they are non-180° domains, which are permitted in the multiaxial TMCM-CrCl<sub>3</sub>. The amplitude images present the magnitude of the piezoresponse of each domain, corresponding well to the phase image. When the piezoresponse is overlaid on the three-dimensional (3D) morphology, it can be seen that the phase and amplitude signals have no obvious correlation with the local topology of the film surface, which excludes the interference from topographic artifacts and further demonstrates the existence of the domain structure (ESI, Fig. S7†).

The switching spectroscopy approach based on PFM (SS-PFM) has been widely used to explore ferroelectric behaviors. SS-PFM is typically performed at a fixed point by applying a pulse-type triangular bias voltage waveform.<sup>52</sup> The hysteresis amplitude and phase loops can be obtained by applying a probing ac voltage while the dc voltage is in the off state. Fig. 4f shows the obtained PFM hysteresis loops as a function of dc voltage. The 180° shifting of the phase signal and the corresponding butterfly-shaped amplitude loop reveal the ferroelectric switching. Domain switching can also be performed with PFM as the PFM tip can be used as a movable top electrode for applying a voltage to the sample. Fig. S8 in the ESI† shows the PFM images before and after two step poling procedures. The 180° phase difference can be observed in the phase images when the upward (ESI, Fig. S8b,† –50 V) and the downward (ESI, Fig. S8c,† +30 V) polarization switching occur. The domain walls can be discerned in the corresponding amplitude images. Thus, the ferroelectricity of TMCM-CrCl<sub>3</sub> has been well characterized by PFM measurements.

## Conclusions

In summary, our work demonstrates that magnetic and electric orderings coexist in a new organic-inorganic hybrid TMCM-CrCl<sub>3</sub>, as the first case of a Cr<sup>2+</sup>-based multiferroic material. It experiences a paraelectric-ferroelectric transition at 397 K with an Aizu notation of 6/*mFm*, triggered by a disorder-order transition of TMCM cations. The strong intra-chain Cr<sup>II</sup>...Cr<sup>II</sup> magnetic couplings indicate its spin-canted antiferromagnetism. These findings will open up a new avenue for multiferroic systems.

## Experimental

### Material synthesis and crystal growth

All reagents and solvents in this experiment were of reagent grade and used without further purification. Trimethylchloromethylammonium chloride (TMCM·Cl) was synthesized by the reaction of equimolar amounts of trimethylamine (30 wt% in water) and dichloromethane in acetonitrile at 60 °C for 24 h. The solvent was removed under reduced pressure to obtain a colorless solid. TMCM-CrCl<sub>3</sub> was prepared by dissolving equimolar amounts of TMCM·Cl and chromium(II) chloride in hot ethanol solution under stirring. Colorless needle-like single crystals were grown by slow evaporation of the clear solution in a glove box. All the experimental measurements of TMCM-CrCl<sub>3</sub> were conducted under a nitrogen atmosphere. The PXRD pattern obtained at 293 K matches well with the result simulated from the single-crystal structure (ESI, Fig. S9†), unraveling the high crystallinity and phase purity. Elemental analysis, calcd (%) for TMCM-CrCl<sub>3</sub>: C, 18.00; N, 5.25; H, 4.15. Found: C, 18.45; N, 5.43; H, 4.25.

### Thin-film preparation

The precursor solution of TMCM-CrCl<sub>3</sub> was prepared by dissolving 30 mg of crystals in 300 μL of ethanol. Then, 20 μL of



The TGA measurement was performed by using a PerkinElmer TGA 8000. The decomposition temperature of TMCM-CrCl<sub>3</sub> is around 290 °C; see Fig. S10 in the ESI.†

In order to investigate the microscopic ferroelectric polarization, we carried out density functional calculations based on the Berry phase method developed by Kingsmith and Vanderbilt.<sup>53,54</sup> The first-principles calculations were performed within the framework of density functional theory implemented in the Vienna *ab initio* Simulation Package (VASP).<sup>55,56</sup> The energy cutoff for the expansion of the wave functions was fixed at 550 eV and the exchange–correlation interactions were treated within the generalized gradient approximation of the Perdew–Burke–Ernzerhof type.<sup>57</sup> For the integrations over the  $k$ -space we used a  $4 \times 3 \times 2$   $k$ -point mesh. The experimental crystal structure was used as the ground state for evaluating the ferroelectric polarization. The rotation of the TMCM cations and the displacement of the  $\text{CrCl}_3$  framework are realized by matrix transformation of the coordinates using Microsoft Excel.

Ren-Gen Xiong and Song Gao devised and developed the project. Yong Ai and Rong Sun performed the experiments. All the authors analysed the data, discussed the results and participated to the manuscript.

## Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (21991140 and 21831004).

- 1 S. Horiuchi and Y. Tokura, *Nat. Mater.*, 2008, **7**, 357–366.
- 2 P.-F. Li, W.-Q. Liao, Y.-Y. Tang, W. Qiao, D. Zhao, Y. Ai, Y.-F. Yao and R.-G. Xiong, *Proc. Natl. Acad. Sci. U. S. A.*, 2019, **116**, 5878–5885.
- 3 C. Qiu, B. Wang, N. Zhang, S. Zhang, J. Liu, D. Walker, Y. Wang, H. Tian, T. R. Shrout and Z. Xu, *Nature*, 2020, **577**, 350–354.
- 4 J. Scott, *science*, 2007, **315**, 954–959.
- 5 C. Shi, L. Ye, Z.-X. Gong, J.-J. Ma, Q.-W. Wang, J.-Y. Jiang, M.-M. Hua, C.-F. Wang, H. Yu and Y. Zhang, *J. Am. Chem. Soc.*, 2019, **142**, 545–551.
- 6 Y.-M. You, W.-Q. Liao, D. Zhao, H.-Y. Ye, Y. Zhang, Q. Zhou, X. Niu, J. Wang, P.-F. Li and D.-W. Fu, *Science*, 2017, **357**, 306–309.
- 7 M. Bichurin, V. Petrov, S. Priya and A. Bhalla, *Adv. Condens. Matter Phys.*, 2012, **2012**, 129794.

- 8 W. Eerenstein, N. Mathur and J. F. Scott, *Nature*, 2006, **442**, 759–765.
- 9 J. Scott, *Nat. Mater.*, 2007, **6**, 256–257.
- 10 L. Ju, T. Sabergharesou, K. G. Stampelcoskie, M. Hegde, T. Wang, N. A. Combe, H. Wu and P. V. Radovanovic, *J. Am. Chem. Soc.*, 2012, **134**, 1136–1146.
- 11 C.-Y. Kuo, Z. Hu, J. Yang, S.-C. Liao, Y. Huang, R. Vasudevan, M. Okatan, S. Jesse, S. V. Kalinin and L. Li, *Nat. Commun.*, 2016, **7**, 1–7.
- 12 S. A. Larregola, J. C. Pedregosa, M. Algueró, R. Jiménez, M. García-Hernandez, M. T. Fernandez-Diaz and J. A. Alonso, *Chem. Mater.*, 2012, **24**, 2664–2672.
- 13 H. Liu and X. Yang, *Ferroelectrics*, 2017, **507**, 69–85.
- 14 J. Wang, J. Neaton, H. Zheng, V. Nagarajan, S. Ogale, B. Liu, D. Viehland, V. Vaithyanathan, D. Schlom and U. Waghmare, *Science*, 2003, **299**, 1719–1722.
- 15 T. Kimura, S. Kawamoto, I. Yamada, M. Azuma, M. Takano and Y. Tokura, *Phys. Rev. B*, 2003, **67**, 180401.
- 16 N. Hur, S. Park, P. Sharma, J. Ahn, S. Guha and S.-W. Cheong, *Nature*, 2004, **429**, 392–395.
- 17 M. Fiebig, T. Lottermoser, D. Fröhlich, A. V. Goltsev and R. V. Pisarev, *Nature*, 2002, **419**, 818–820.
- 18 S.-W. Cheong and M. Mostovoy, *Nat. Mater.*, 2007, **6**, 13–20.
- 19 N. A. Hill, *J. Phys. Chem. B*, 2000, **104**, 6694–6709.
- 20 V. B. Lu, F. M. Gribble and F. Reimann, *Nutrients*, 2021, **13**, 883.
- 21 Y. Shen, G. Cosquer, H. Ito, D. C. Izuogu, A. J. Thom, T. Ina, T. Uruga, T. Yoshida, S. Takaishi and B. K. Breedlove, *Angew. Chem., Int. Ed.*, 2020, **132**, 2420–2427.
- 22 T. Hang, W. Zhang, H.-Y. Ye and R.-G. Xiong, *Chem. Soc. Rev.*, 2011, **40**, 3577–3598.
- 23 P.-P. Shi, Y.-Y. Tang, P.-F. Li, W.-Q. Liao, Z.-X. Wang, Q. Ye and R.-G. Xiong, *Chem. Soc. Rev.*, 2016, **45**, 3811–3827.
- 24 W. Zhang and R.-G. Xiong, *Chem. Rev.*, 2012, **112**, 1163–1195.
- 25 B. Huang, J.-Y. Zhang, R.-K. Huang, M.-K. Chen, W. Xue, W.-X. Zhang, M.-H. Zeng and X.-M. Chen, *Chem. Sci.*, 2018, **9**, 7413–7418.
- 26 W. Li, Z. Wang, F. Deschler, S. Gao, R. H. Friend and A. K. Cheetham, *Nat. Rev. Mater.*, 2017, **2**, 1–18.
- 27 B. Saporov and D. B. Mitzi, *Chem. Rev.*, 2016, **116**, 4558–4596.
- 28 G.-C. Xu, X.-M. Ma, L. Zhang, Z.-M. Wang and S. Gao, *J. Am. Chem. Soc.*, 2010, **132**, 9588–9590.
- 29 D. W. Fu, W. Zhang, H. L. Cai, Y. Zhang, J. Z. Ge, R. G. Xiong, S. D. Huang and T. Nakamura, *Angew. Chem., Int. Ed.*, 2011, **50**, 11947–11951.
- 30 L. C. Gómez-Aguirre, B. n. Pato-Doldán, J. Mira, S. Castro-García, M. A. Señaris-Rodríguez, M. Sánchez-Andújar, J. Singleton and V. S. Zapf, *J. Am. Chem. Soc.*, 2016, **138**, 1122–1125.
- 31 G.-C. Xu, W. Zhang, X.-M. Ma, Y.-H. Chen, L. Zhang, H.-L. Cai, Z.-M. Wang, R.-G. Xiong and S. Gao, *J. Am. Chem. Soc.*, 2011, **133**, 14948–14951.
- 32 D. Di Sante, A. Stroppa, P. Jain and S. Picozzi, *J. Am. Chem. Soc.*, 2013, **135**, 18126–18130.
- 33 A. Stroppa, P. Jain, P. Barone, M. Marsman, J. M. Perez-Mato, A. K. Cheetham, H. W. Kroto and S. Picozzi, *Angew. Chem., Int. Ed.*, 2011, **50**, 5847–5850.
- 34 H.-L. Cai, Y. Zhang, D.-W. Fu, W. Zhang, T. Liu, H. Yoshikawa, K. Awaga and R.-G. Xiong, *J. Am. Chem. Soc.*, 2012, **134**, 18487–18490.
- 35 R. Samantaray, R. J. Clark, E. S. Choi and N. S. Dalal, *J. Am. Chem. Soc.*, 2012, **134**, 15953–15962.
- 36 R. Samantaray, R. J. Clark, E. S. Choi, H. Zhou and N. S. Dalal, *J. Am. Chem. Soc.*, 2011, **133**, 3792–3795.
- 37 M. Maczka, K. Pasinska, M. Ptak, W. Paraguassu, T. A. da Silva, A. Sieradzki and A. Pikul, *Phys. Chem. Chem. Phys.*, 2016, **18**, 31653–31663.
- 38 M. Maczka, A. Gagor, M. Ptak, W. Paraguassu, T. A. da Silva, A. Sieradzki and A. Pikul, *Chem. Mater.*, 2017, **29**, 2264–2275.
- 39 Z. Hu, H. Zhao, Z. Cheng, J. Ding, H. Gao, Y. Han, S. Wang, Z. Xu, Y. Zhou, T. Jia, H. Kimura and M. Osada, *Phys. Chem. Chem. Phys.*, 2020, **22**, 4235–4239.
- 40 J. M. Bermudez-Garcia, M. Sanchez-Andujar, S. Castro-Garcia, J. Lopez-Beceiro, R. Artiaga and M. A. Senaris-Rodriguez, *Nat. Commun.*, 2017, **8**, 15715.
- 41 J. P. Zhao, J. Xu, S. D. Han, Q. L. Wang and X. H. Bu, *Adv. Mater.*, 2017, **29**, 1606966.
- 42 L. Canadillas-Delgado, O. Fabelo, J. A. Rodriguez-Velamazan, A. Stunault, J.-P. Zhao, X.-H. Bu and J. Rodriguez-Carvajal, *Iucrj*, 2020, **7**, 803–813.
- 43 A. Stroppa, P. Barone, P. Jain, J. M. Perez-Mato and S. Picozzi, *Adv. Mater.*, 2013, **25**, 2284–2290.
- 44 H.-Y. Liu, H.-Y. Zhang, X.-G. Chen and R.-G. Xiong, *J. Am. Chem. Soc.*, 2020, **142**, 15205–15218.
- 45 K. Aizu, *ecirc and itsiro*, *J. Phys. Soc. Jpn.*, 1969, **27**, 387–396.
- 46 W.-Q. Liao, Y.-Y. Tang, P.-F. Li, Y.-M. You and R.-G. Xiong, *J. Am. Chem. Soc.*, 2018, **140**, 3975–3980.
- 47 D. Di Sante, A. Stroppa, P. Jain and S. Picozzi, *J. Am. Chem. Soc.*, 2013, **135**, 18126–18130.
- 48 N. A. Spaldin, *J. Solid State Chem.*, 2012, **195**, 2–10.
- 49 R. Resta and D. Vanderbilt, *Physics of Ferroelectrics: A Modern Perspective* 2007, vol. 105, pp. 31–68.
- 50 E. A. Boudreaux and L. Mulay, *Theory and applications of molecular paramagnetism*, John Wiley & Sons, 1976.
- 51 W. Haase, *Bunsen-Ges. Phys. Chem., Ber.*, 1988, **92**, 453.
- 52 O. Kwon, D. Seol, H. Qiao and Y. Kim, *Adv. Sci.*, 2020, **7**, 1901391.
- 53 R. King-Smith and D. Vanderbilt, *Phys. Rev. B*, 1993, **47**, 1651.
- 54 D. Vanderbilt and R. King-Smith, *Phys. Rev. B*, 1993, **48**, 4442.
- 55 G. Kresse and J. Furthmüller, *Phys. Rev. B*, 1996, **54**, 11169.
- 56 G. Kresse and J. Furthmüller, *Comput. Mater. Sci.*, 1996, **6**, 15–50.
- 57 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.

