

Faraday Discussions

Accepted Manuscript



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

This article can be cited before page numbers have been issued, to do this please use: J. M. Walker, M. A. Gomez Gonzalez, J. Ihli and J. E. Parker, *Faraday Discuss.*, 2025, DOI: 10.1039/D5FD00037H.

Following the Faraday meeting data will be made available through zenodo and a link to the URL provided. Before the meeting data is available on request

[View Article Online](#)
DOI: 10.1039/D5FD00037H

Open Access Article. Published on 01 2025. Downloaded on 2025/5/28 21:55:34.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.



Exploiting nanoprobe X-ray techniques for imaging of biomineralisation; chemical, structural and *in situ* opportunities

[View Article Online](#)

DOI: 10.1039/D5FD00037H

Keywords: X-ray; nanoprobe; *in situ* liquid; XRF; ptychographyJessica M. Walker¹, Miguel A. Gomez Gonzalez¹, Johannes Ihli² and [Julia E. Parker¹](#)¹Diamond Light Source, Diamond House, Harwell Science and Innovation Campus, Didcot, Oxfordshire, OX11 0DE, UK.²Department of Materials, University of Oxford, Parks Road, Oxford, OX1 3PH, UK.

Abstract

Advances in X-ray nanoprobe beamlines at synchrotrons across the world present exciting opportunities for rich multimodal imaging of biomineral structures and their formation processes. The combination of techniques provides a sensitive probe of both chemistry and structure, making X-ray nanoprobe an important tool for investigating crystallite growth and orientations, interfaces and assembly of building blocks into hierarchical structures. A discussion of these capabilities is presented with reference to recent examples using a range of nanoprobe imaging techniques for investigating enamel structure, as well as coccolith properties. Key opportunities for the use of X-ray nanoprobe lie in exploiting the penetrating power and coherence properties of synchrotron X-rays in order to image *in situ* processes or apply coherent diffractive imaging techniques to obtain higher resolutions. To this end initial results demonstrating the observation of calcium phosphate mineralisation, in a liquid environment, using nano-X-ray fluorescence mapping are presented, and the role of X-ray dose and beam induced effects is considered. Finally novel results from tomographic ptychography imaging of a *Mytilus edulis* mussel shell calcite prisms are discussed, where the segmentation of the phase density into organic and mineral content give insights into the mechanisms underlying mineral prism formation and the role of the organic matrix in biomineralisation.

1. Introduction

Biominerals are inorganic materials synthesised by living organisms, composed of a wide range of minerals such as calcium carbonate, hydroxyapatite and silica. From the shells of marine molluscs to the bones of vertebrates, biominerals demonstrate remarkable diversity in composition and morphology, serving essential structural, protective, and functional roles^{1,2}. The composite nature of biominerals, comprising both mineral crystalline phase and organic matrix, imparts unique properties, such as the mechanical strength and fracture toughness of mussel shell when compared to synthetic equivalents^{3,4, 5}.

Organisms are able to exert precise control over the mineralisation process, controlling the crystal phase and polymorph formed (even switching between polymorphs in a single structure) and the resulting structure and morphologies. It is proposed that this control occurs through; regulating of the chemical environment around cells; mediating ions and precursor availability; controlling pH levels; confinement of processes; and the presence of organic matrices which can act as nucleation and ion binding sites^{6,7}. Observations of biomineralisation processes, and the identification of stable amorphous precursor phases in biominerals, has contributed to a plethora of discussions about non classical crystallisation pathways, encompassing prenucleation clusters, orientated attachment and mesocrystallinity^{7,8}. Hence, there continues to be much interest in imaging mineralisation processes, across multiple lengths and timescales, in order to gain further insights into the underlying mechanisms.



This fine control over mineralisation is often exhibited as exquisite structures and forms, from coccolithophore calcite formation to the spiral of narwhal tusk, with highly organised hierarchical structures⁹. This hierarchical structure contributes to the superior mechanical properties and functionality of biominerals. Understanding the organisation of biominerals, across the different structural levels, is therefore important for a thorough understanding of formation processes, properties, and development of biomimetic approaches for materials development¹⁰.

The structural complexity of biominerals presents significant challenges for characterisation. Understanding both structure and formation of these complex materials requires a range of characterisation and imaging techniques across multiple length scales and modalities. Here X-ray imaging can be used to complement other microscopies (such as light, Raman and electron microscopy) and provide a non-destructive means of probing the structure and composition of biominerals.

With focussed X-ray beam sizes of 25-100 nm, combined with the increased spatial resolution achievable through coherent diffractive imaging techniques such as ptychography, the experimental envelope of X-ray nanoprobe bridges the resolutions and fields of view between transmission electron microscopies and microscale techniques, whilst the penetrating power of hard X-rays increases the availability of options for *in situ* imaging studies. X-ray nanoprobe allow a combination of techniques including nano-X-ray fluorescence (n-XRF), spectroscopy, nano-X-ray diffraction (n-XRD), and advanced phase imaging, which can be applied to biomineralisation studies, revealing details of nanoscale elemental compositions, structures and morphologies¹¹.

A key advantage of using X-rays is the ability to penetrate 'thicker' sample environments in order to image *in situ* processes^{12,13,14}. Of particular interest for biomineralisation is the ability to observe crystallisation processes and kinetics. Here, the design challenges of *in situ* liquid cells are discussed, and initial results demonstrating the observation of calcium phosphate mineralisation in a liquid environment, using n-XRF mapping are presented. These results illustrate the potential advantages and role of *in situ* nanoprobe techniques for mineralisation studies and highlight key aspects for future development and study. These include the role played by X-ray dose and beam induced effects, an important consideration when designing experimental approaches and interpreting results which has not yet been widely studied for X-ray nanoprobe *in situ* experiments.

The final factor in exploiting X-ray nanoprobe for biomineral imaging lies in the direction of applying coherent imaging techniques. Tomographic ptychography, a scanning coherent diffractive imaging technique, enables quantitative 3D visualisation of electron density, making it highly suited for exploring the impact of organic-mineral interfaces on structure and properties. Novel results from tomographic ptychography imaging of a *Mytilus edulis* mussel shell calcite prism are discussed, where the nanoscale segmentation of the phase density into organic and mineral content give insights into the mechanisms underlying mineral prism formation and the role of the organic matrix in biomineralisation.

2. Hard X-ray Nanoprobe Imaging

X-ray nanoprobe beamlines are found at most synchrotrons worldwide¹⁵⁻²¹, often forming a central role in facilities' upgrade programs as they are well positioned to exploit the increased brilliance and coherence of a fourth generation light source. In the last 10-15 years advances in X-ray optics have led to ever decreasing beam sizes, and hence higher image resolutions. Beamlines use highly specialised optics (including zone plates, Kirkpatrick Baez mirrors, multilayer laue lens) where focusing to sub 10nm X-ray beam sizes have been demonstrated²², and 10-50 nm are routinely achieved²³⁻²⁵ at



operational beamlines, which, combined with high stability environments and precision scanning stages, make a unique probe for examining elemental, chemical and structural information of materials.

Article Online
DOI: 10.1039/D5FD00037H

Nanoprobes are multi-modal probes, allowing simultaneous imaging using a combination of different techniques, at the same resolution, on the same sample. X-ray fluorescence (XRF) enables the mapping of elemental distributions in a sample, providing information on material compositions and heterogeneity. Phase contrast imaging techniques (such as differential phase contrast imaging (DPC))²⁶ gives information on the sample morphology and density. This is often crucial in biological samples to provide a context for the elemental XRF maps, where lighter elements (including carbon, nitrogen and oxygen) are not observed. Thus a combination of DPC and XRF imaging can provide simultaneous imaging of the cellular structures and the distribution of metal nanoparticles or metallo-organic drugs, for example when investigating treated cancer cells^{27,28}. X-ray diffraction (XRD) probes the crystalline, atomic structure of the materials, and can be used to fingerprint the presence of different phases, such as mineral distributions in samples or, with a more detailed analysis, map lattice strain variations.

By repeating n-XRF maps at different energies the technique can be extended to give X-ray Absorption Near Edge Structure (XANES) spectroscopy maps (nano-XANES). 2D n-XRF maps are collected on a region at energies through an elemental absorption edge. The elemental maps extracted from the XRF spectra at each energy are aligned and stacked to give a 3D image stack where each pixel (x, y) has a third coordinate, energy. The nano-XANES can be analysed, typically through principal component and cluster analysis, to group the spectra based on spectral similarities followed by fitting to reference data, to extract amounts and locations of distinct species. Repeating scans for different energies increases substantially the time and X-ray dose required to image a sample, limiting the use of this technique for *in situ* or biological samples. The X-ray dose and time can be reduced by the application of a variety of approaches, including sparse energy sampling²⁹ or undersampling the raster scans³⁰. Implementation of these options begins to open the possibility of applying nano-XANES approaches to beam and time sensitive experiments.

The coherent nature of nanoprobe X-rays allows the application and development coherent diffraction imaging techniques such as ptychography³¹. In ptychography, far field diffraction patterns are collected at a series of overlapping scan positions. An iterative phase retrieval algorithm is used to recover the phase and amplitude of the scattered wave, reconstructing both phase and adsorption image of the sample. Importantly, the image resolution is not limited by the size of the X-ray beam, offering the possibility of achieving higher resolution images than probe-limited techniques such as DPC.

These techniques can be extended to three dimensions through tomography – collecting maps or projections at a series of different angles as the sample is rotated and reconstructing to form a 3D volume. Current challenges for the implementation of tomographic techniques at nanoprobes centre around sample preparation and speed of acquisition. The demands of sample preparation, to produce a 10-20 μm pillar, extracted from a specific region in a larger sample and mounted on a pin, require specialised approaches, such as FIB-SEM, and dedicated time and expertise. Smaller samples are currently required in order to keep the sample in the focus of the beam and reduce the inherent scanning time limitations. In most cases the limitation on scanning speed is not a flux but rather a hardware, controls and detector limitation. However, desire to extend to larger volume imaging means an increase in scanning speeds is a current development push³². Overall, combining information from different X-ray modalities, through for example correlative ptychographic tomography and n-XRF, or n-XRF and n-XRD, is a powerful approach for imaging a wide range of materials, from biological cells³³, to catalyst³⁴ and battery³⁵ particles, and historic paint samples³⁶.



2.1 I14 – Diamond’s Hard X-ray Nanoprobe

Beamline I14 is the hard X-ray nanoprobe beamline at Diamond Light Source¹⁶. Figure 1(a) outlines the beamline components; the beamline is 185 m long from the source (a U22 undulator) to the sample position with the major optical components inside the main synchrotron ring building. The first mirror horizontally collimates the beam onto the secondary source aperture, vertically the source is imaged directly. The beam is monochromated by a Si (111) horizontal bounce double crystal monochromator, to tune the X-ray energy within the range 5 – 20 keV.

The experimental hutch is located in a purpose built external building. At the endstation, figure 1(b), the X-ray beam is focused to 50 nm at the sample position (1) using a pair of in vacuum nano focusing KB mirrors. The sample, typically on a silicon nitride membrane window, or TEM grid is mounted onto a magnetic holder and placed in the sample position (1). The sample spigot is attached via a kinematic mount to the scanning stages (2). The kinematic mounting system, combined with the long working distance focus of the KB optic, and in air environment, provides a flexible space for incorporating bespoke sample mounting solutions and a variety of *in situ* environments and facilitating easy changeover of experimental setups.

The scanning stage is a novel stage design concept, a Delta Robot³⁷. The delta robot uses three orthogonal voice coils, which actuate parallelogram flexures for a 3mm travel range in x, y and z directions. The design enables high speed scanning at nm precision over mm travel ranges, with space and load capacity for flexible setups and sample environments. On top of the delta robot, underneath the kinematic mount, is a rotation stage to enable tomography measurements.

Once mounted a sample is aligned to the beam focus and region of interest found using the retractable sample alignment microscope (3). XRF data are collected in backscatter geometry using a four-element silicon drift detector (4). Downstream of the sample scattered or transmitted X-ray can be collected for DPC, ptychography or XRD analysis using silicon pixellated photon counting detectors; a quad merlin (Quantum Detectors), Excalibur 3M or an Eiger 500K (Dectris). These detectors are mounted on independent translation rails on a movable granite table to facilitate alignment and changeover between detector distances and setup – e.g.. for ease of switching between DPC and XRD data collections in one experiment. Setup up of scanning regions (maps), and viewing of live data collections, is facilitated through an intuitive interface to the beamline controls system using a mapping GUI in the data acquisition system.

The capability of X-ray nanoprobe beamlines to collect correlative data across different modalities, across three dimensional and *in situ* experiments, and developments in faster scanning, present challenges in data processing and analysis. I14 has therefore placed a great deal of emphasis on ease of experiment and automated data processing pipelines, to enable live processing on Diamond’s high performance computing cluster during a scan of; elemental maps from XRF spectra; processing of DPC data to give a quantitative phase image; stacking and alignment of XANES data; integration of 2D XRD images to 1D patterns and automated submission of ptychography reconstructions. This is complemented by offline processing tools using a web GUI for workflow submissions.

2.2 Hard X-ray Nanoprobe Imaging of Biomineralization at I14

These capabilities, combined with the beamline’s flexibility make I14 a powerful tool for imaging of biominerals. This strength can be further exploited by combining with complementary techniques, such as electron microscopy for a multi length scale imaging approach.

View Article Online
DOI: 10.1039/C9FD00037H



X-ray nanoprobe measurements at I14 were combined with soft X-ray ptychography, electron microscopy and larger scale X-ray tomography to investigate the chemical and structural properties of carious enamel^{38,39}. The hierarchical structure of human dental enamel, with orientated hydroxyapatite (Hap) crystals arranged into rod and interrod regions where the nanoscale arrangement contributes to the mechanical strength of the enamel⁴⁰. Demineralization during caries formation leads to chemical and structural changes which reduce the stiffness and strength of the enamel. Besnard et al.³⁹ investigated these changes in FIB-lamellae extracted from locations in tooth enamel corresponding to normal and demineralised areas. Using a I14, n-XRF mapping revealed calcium chemical gradients across the rod and interrod areas corresponding to different demineralization rates. The chemical information was correlated with crystal orientations extracted from n-XRD measurements and structural changes observed in DPC. Higher resolution images of the same sample using soft X-ray tomography (at Diamond's I08 beamline) allowed alignment of the n-XRF maps to start to reveal details of crystallite orientation gradients within the enamel.

Coccolithophores play an important role in global biogeochemical cycles⁴¹. They produce a calcium carbonate exoskeleton, composed of coccoliths. Coccoliths are arrays of nanoscale crystals that form intracellularly, a key example of the fine control biomineralising organisms exhibit over the chemistry and morphology of their mineral phases. Understanding their formation necessitates information on elemental distribution and speciation at a nanoscale level. n-XRF tomography of a coccolith (the lopadoliths of *Scyphosphaera apsteinii*) at I14 revealed an uneven distribution of strontium⁴², with stripes of different concentrations, as shown in figure 4. This is in contrast with current Sr fractionation models which predict an even distribution. The n-XRF tomography was complemented by nano-XANES analysis of the same sample to show that Sr resides in a Ca site in the calcite lattice in both high and low Sr stripes, confirming a central assumption of current Sr fractionation models.

Nano-XANES at I14 has also been used, in combination with DPC and nano-XRF to investigate magnetosome formation at the single-cell level in magnetotactic bacteria (MTB)⁴³. MTB synthesize single-domain magnetic nanoparticles composed of magnetite (Fe_3O_4) or greigite (Fe_3S_4) within organelles known as magnetosomes, yet the mechanisms of biomineralization are still unclear. Recent work suggests a large fraction of intracellular iron, at least partly composed of ferrous species, is not incorporated into magnetosomes⁴⁴. Wild-type *M. gryphiswaldense* MSR-1 bacteria and a genetic variant lacking ferritin proteins were studied under varied iron concentrations and at different stages of magnetosome formation. DPC and nano-XRF mapping was first used to reconstruct both organic and inorganic components of bacterial cells to identify intracellular regions. Fe K-edge nano-XANES was then used to differentiate magnetosome particles from other intracellular iron species and determine their relative amounts, figure 3, confirming a significant presence of intracellular iron species distinct from magnetite during biomineralization.

3. A liquid cell *in situ* study of calcium phosphate precipitation

The I14 endstation was designed to have flexibility to mount a variety of different *in situ* sample environments, to be able to incorporate thicker or larger sample environments; hard X-rays are able to penetrate much thicker materials than electrons or soft X-rays. However, the thickness of a sample or *in situ* cell has an impact on the achievable resolution of the technique, as beam is scattered through more sample material or the sample thickness exceeds the depth of field of the X-ray focus. The design of a sample environment must also be carefully considered so as not to import drift or vibrations to the measurement, the design parameters being similar to those of environments developed for TEM *in situ* studies. Given the complementarity of nanoprobe and TEM techniques and the desire for correlative approaches, it is possible to incorporate TEM sample environments into X-ray nanoprobe¹²⁻¹⁴. I14 have developed mounts to hold commercial TEM MEMS chip devices, allowing



the easy use of existing systems for both gas and liquid flow. A schematic of liquid cell chips made up of 2 silicon nitride windows to form a sandwich structure is shown in figure 4(a). To avoid window bulging and thick liquid layers preventing transmission of electrons, TEM liquid cell chips have small (50 x 50 μm) window areas and thickness spacings of a 200 nm or less. When considering crystallisation experiments this presents a confined environment which may influence system kinetics through limited diffusion of ions or on morphologies of crystals formed. In this work we were able to relax these confinement effects to some extent by using chips with larger windows and a much thicker (8 μm) spacing. Assembled chips are mounted in a holder, either the removeable tip piece of a TEM holder (DENS systems) or a beamline mount (Protochips), on a custom kinematic mounted plate on the I14 stages, figure 4(b).

3.1 Materials and Methods

A calcium phosphate (CaP) mineralisation solution was prepared by mixing equal volumes of a Ca solution (1.7 mM CaCl_2 in 125 mM NaCl, 50 mM Tris, pH 7.40) and phosphate solution (9.5 mM Na_2HPO_4 in 125 mM NaCl, 50 mM Tris (pH 7.40)). The same solution conditions as used by Wang et al.⁴⁵ All reagents were purchased from Sigma-Aldrich and dissolved in deionised water. After mixing, the CaP solution was immediately loaded into a 1 ml glass syringe and a syringe pump used to flow the solution through the assembled liquid cell. The Ca-K α fluorescence signal was monitored using n-XRF and once signal was observed in the cell window area flow was stopped and n-XRF mapping commenced.

Repeat n-XRF maps were collected on beamline I14, Diamond Light Source¹⁶ using a 50 nm focused X-ray beam at an energy of 12 keV. XRF spectra were collected using a 4 element silicon drift detector in backscatter geometry. Ca elemental maps were produced by integrating the intensity in the XRF spectra over a 200eV window around the Ca-K α fluorescence peak (3.6 keV). The P signal can be mapped from the same spectra, however due to the lower X-ray energy and the absorption by the liquid and air path the signal is much weaker and so is not presented here, although the distributions match those of Ca.

3.2 *In situ* crystallisation results and discussion

Figure 5 shows a time series of Ca maps taken over 3 hours. After 1 hour, the CaP appears to have formed an extended network, of small nanoscale particles (it is possible these are clusters of ions or amorphous precursors, or crystallites). Over a further 1-2 hours these can be seen to transform and growth of denser larger particles occurs. After 3 hours, additional smaller crystals can be seen to form at the bottom left of the field of view. Integrating the total Ca signal intensity in the two regions outlined in figure 6 (a) for an area where these denser particles formed and one where it did not, show that the intensity in Region 1 increased sharply 100 minutes after mixing, see figure 6 (b). The intensity in Region 2 does not change, suggesting that the CaP in these regions is not being redissolved in order to precipitate the larger structure formation observed in Region 1, diffusions of ions over larger distances must be occurring.

The total Ca signal intensity in the entire mapped area decreased over time and we note that after 24 hours, the formed crystals in the field of view dissolved, and other larger crystals were found nearby when scanning nearby areas – raising the question of the role of beam effects in the dissolution process. Existing models of X-ray dose effects on liquids suggest that X-ray exposure can contribute to radiolysis of the solution, and generate radicals which change the local solution pH. Over time – and in the absence of flow – dispersion of these species is diffusion limited, so effects will accumulate.



These initial results can be compared to a TEM *in situ* liquid cell study of CaP crystallisation⁴⁵. As the same solution concentrations were used, similar kinetics might therefore be expected in the absence of beam induced effects and any confinement effects due to the different cell geometries. Wang et al. observed branched morphologies after 1 hour, these appear to be very similar in nature to the structures observed here. It is clear however that *in situ* TEM offers improved resolution, both spatial and temporal, above these initial nanoprobe measurements for imaging biomineral formation mechanisms⁴⁶⁻⁴⁹. However, we suggest that they can be complementary in a multiscale approach; access to larger fields of view available, as well as the chemical information that can be extracted, is important for examining at the mesoscale the assembly into hierarchically ordered structures. The greater flexibility offered in terms of sample environments opens interesting avenues in terms of customised microfluidic cells for controlling crystallisation, and bridging the gap between TEM and microscale microscopy techniques.

In order to progress from these initial results an improved understanding, and mitigation, of beam effects is required, building on ongoing modelling for electron dose effects including consideration of scanning paths, damage models and propagation. Improvements in speed can also be achieved by various routes, for example by continued application and development of sparse sampling approaches^{29,30}.

4. A ptychographic tomography study of mussel shell calcite prisms

Mussel shell has a structural toughness which serves to protect them from prey. Shells consist of three layers, from the inner nacreous layer, the prismatic layer and the outer periostracum organic layer. The structural toughness arises from a combination of the different microstructures of the layers and their thickness^{50,51}. In the prismatic layer, calcite prisms, surrounded by an interprismatic organic matrix, are orientated at an angle to the shell surface. Here we investigate the internal structure of a calcite prism, using ptychography, in order to determine the relationship between the mineral phase and organic component.

4.1 Materials and Methods

Sections of *Mytilus edulis* shell, approximately 10 x 10 mm, selected from regions where no, or only a very thin nacreous layer was observed, were washed in deionised water and the outer organic periostracum removed. Sections were soaked in 4% NaOCl solution for 96 hours in order to dissolve the interprismatic organic matrix and separate individual calcite prisms. Once separated the solution was filtered and the isolated prisms washed with DI water. Prisms were imaged using a SEM (Hitachi Tabletop TM 1000). Isolated prisms were selected using optical microscopy and mounted on a cSAXS OMNY tomography pin⁵².

Ptychographic X-Ray tomography experiments were carried out at the cSAXS beamline of the Swiss Light Source⁵³. The photon energy was 6.2 keV. A Fresnel zone plate 220 μm in diameter with an outermost zone width of 60 nm was coherently illuminated, and the sample placed 1.2 mm downstream of the zone plate focal point. The sample was mounted in the in vacuum cryo-ONMY scanning instrument at -180 °C and scanned through the X-ray beam with a Fermat spiral covering 20 x 10 μm with a step size of 1.3 μm . Far-field coherent diffraction patterns were acquired with exposure times of 0.1 s per point using a Pilatus detector with 172 μm pixel size at a sample- detector distance of 7.342 m. A flight tube between sample and detector was used to reduce air scatter and absorption effects. 1000 angular tomography projections were acquired.



Ptychographic reconstructions were obtained using the difference map algorithm⁵⁴, with maximum-likelihood refinement⁵⁵. Tomographic reconstruction of the phase images was carried out following alignment using a modified filtered back-projection algorithm as described by Guizar-Sicairos⁵⁵. Article Online
DOI: 10.1039/D5FD00037H

The X-ray dose imparted to a prism sample during tomogram acquisition was estimated to be on the order of $10^8 - 10^9$ Gy. The estimated dose is based on the average area flux density of each scan and the assumed mass density of the specimen, assuming a composition of calcite and chitin.

The half-period spatial resolution of ptychographic tomograms was estimated by Fourier shell correlation (FSC). The threshold criteria for the FSC was the $\frac{1}{2}$ bit criteria. From this analysis the resolution is estimated to be 75 nm.

4.3 Ptychographic Tomography results and discussion

SEM images of calcite prisms extracted from *Mytilus edulis* shell are shown in figure 7. It can be seen that there exist what appear to be elongated isolated crystals, of needle-like shape. This is in agreement with previous results which demonstrate shell prismatic layer consists of an array of crystallites, oriented along their long axis, within an organic matrix. Individual prisms are of the order 40 μm long and 5 μm diameter. Larger aggregates can also be found, presumably where the treatment to remove interprismatic organics has not fully removed the organic component. Isolated prisms, similar to those shown in figure 7, were selected for imaging using ptychographic tomography

Images from the ptychographic tomography reconstruction of the *Mytilus edulis* calcite prism are shown in figure 8 (a)-(d). What was assumed to be a single prism here when mounting is in fact multiple smaller prisms, with their longitudinal axis co-aligned with the long axis of the larger needle shaped prism being imaged. In contrast to micro- X-ray CT results examining the grain growth of *Pinna nobilis* calcite prisms⁵⁶, where each prism was observed to be a regular polygonal shape, these individual smaller prisms are much more irregular, figure 8 (c) and (d). This may be due to interspecies variation (*Pinna nobilis* prisms are much larger than those of *Mytilus edulis*), the region of the shell from which the prisms were extracted (e.g. fresh growth vs. fully formed crystals) or the differing resolutions and length scales accessible via the different imaging techniques.

The 3D volume was segmented to separate the intensity based on the outermost 100nm of each prism (figure 8 (a) and (b) compared to the internal prism structure. This reveals the intricate web of organic matrix around each individual prism, in agreement with electron microscopy studies that have imaged these prismatic envelopes in *Pinna nobilis* and *Atrina rigida* prismatic layers^{57,58}. Here we are able to observe them in 3D without prior dissolution of the mineral component, this enables visualisation of the close link between organic and mineral at the outer regions of the prisms.

An advantage of ptychography is that the measured intensity corresponds to a quantitative electron density, this is shown for the internal prism and outermost 100 nm in the histogram in figure x (e). Comparing to the known electron densities for chitin and calcite suggest the outermost layer is a good match to the electron density of chitin. The mineral phase of the prisms is however lower electron density than calcite, which is presumably due to differences in crystallinity and packing density, hydration and presence of water as well as organics in the crystal structure⁵⁹.

The electron density can be plotted with distance from the centre of a prism, as an average across the prisms imaged, figure 8 (d). In addition to the higher organic content at the outer 100nm, it can be seen that the inner 300 nm core of the prisms has a much lower electron density. The organic content of each voxel can be estimated using the known electron densities, segmentation based on 55-75 vol%



organic is shown in figure 8 (e) and (f). The presence of an organic rich core running through the centre of each prism can be clearly seen.

View Article Online

DOI: 10.1039/D5FD00037H

The observations of an organic web like prismatic envelope, and a central organic core is suggestive of a formation mechanism in which calcite nucleation occurs within a dense organic fluid precursor phase, with the crystal growing to fill the space defined by the prismatic envelope, resulting in a calcite prism with high incorporated organic content. This is in broad agreement with existing results observing the organic web and a dense intra crystalline network of chitin within *Atrina rigida* calcite prisms^{58,60}.

5. Conclusions

The advancements in X-ray nanoprobe beamlines have opened new frontiers for multimodal imaging of biomineral structures, offering insights into their formation and hierarchical organisation. By leveraging the combination of X-ray fluorescence, diffraction, and ptychographic techniques, researchers can probe both the chemical composition and structural arrangement of biominerals at the nanoscale. A particularly promising direction lies in the *in situ* imaging of mineralisation processes, where the penetrating power of synchrotron X-rays enable real-time observations. Initial experiments using n-XRF mapping to monitor calcium phosphate mineralisation in a liquid environment demonstrate the feasibility of tracking biomineralisation dynamics with high spatial resolution. However, careful consideration of X-ray dose effects remains critical to minimize beam-induced artifacts and further developments to improve speeds and optimise scanning pathways is required.

Tomographic ptychography has provided novel insights into the formation mechanisms of *Mytilus edulis* calcite prisms, revealing the distinct contributions of organic and mineral components in biomineralization. These findings underscore the potential role of X-ray nanoprobe in biomaterials research, paving the way for future studies that exploit higher resolution imaging and *in situ* methodologies to deepen our understanding of biomineral formation processes.

6. Conflicts of Interest

There are no conflicts of interest to declare

7. Acknowledgements

We would like to thank Dave Mahoney and Mark Hooper for their design and technical efforts to enable the *in situ* cell mounting and integration. Gea van de Kerkhof is acknowledged for her essential contributions to the liquid cell development work and experimental procedures. Diamond Light Source is acknowledged for beamtime on I14 under proposal mg30893 for the *in situ* liquid cell studies. For the ptychography tomography Aaron Parsons is thanked for advice and support with the planning and experiment and the assistance of the cSAXS team at the Swiss Light Source is gratefully acknowledged, in particular Klaus Wakonig for experiment and data reconstruction, and Mirko Holler and Ana Diaz for OMNY setup.

References

1. Lowenstam, H.A., Weiner, S., On Biomineralization (Oxford University Press, New York, 1989).
2. Mann, S., Biomineralization, Principles and Concepts in Bioinorganic Materials Chemistry (Oxford University Press, 2001)
3. Jackson AP, Vincent JF, Turner RM. The mechanical design of nacre. Proceedings of the Royal society of London. Series B. Biological sciences. 1988 Sep 22;234(1277):415-40.



4. Currey, J.D. The effect of drying on the strength of mollusc shells. *Journal of Zoology* (1979), 188: 301-308.

View Article Online
DOI: 10.1039/D5FD00037H

5. Gao H., Ji B. , Jäger I.L., Arzt E., & Fratzl P., Materials become insensitive to flaws at nanoscale: Lessons from nature, *Proc. Natl. Acad. Sci.* (2003). 100 (10) 5597-5600.

6. Kahil K, Weiner S, Addadi L, Gal A. Ion Pathways in Biomineralization: Perspectives on Uptake, Transport, and Deposition of Calcium, Carbonate, and Phosphate. *J Am Chem Soc.* 2021;143(50):21100-21112.

7. Gilbert P. U. P. A. et al. Biomineralization: Integrating mechanism and evolutionary history. *Sci. Adv.* 8, eabl9653 (2022).

8. Jehannin M., Rao A., and Cölfen H., New Horizons of Nonclassical Crystallization, *Journal of the American Chemical Society* 2019 141 (26), 10120-10136.

9. Seto J , Ma Y , Davis SA , Meldrum F , Gourrier A , Kim YY , Schilde U , Sztucki M , Burghammer M , Maltsev S , Jäger C , Cölfen H., Structure-property relationships of a biological mesocrystal in the adult sea urchin spine., *Proceedings of the National Academy of Sciences* 109, no. 10 (2012): 3699-3704.

10. Fratzl P. Biomimetic materials research: what can we really learn from nature's structural materials?. *J R Soc Interface.* 2007;4(15):637-642.

11. Medjoubi K. , Benzerara K. , Debie J. , Tang E. , Bazin D. , Letavernier E. , Desjardins K. , Somogyi A., State-of-the-art multimodal scanning hard X-ray imaging and tomography sheds light at multiple length-scales on biomineralization related processes, *Frontiers in Environmental Chemistry* (2024), 5, 1339829.

12. Parker, J. E., Gomez-Gonzalez, M., Van Lishout, Y., Islam, H., Duran Martin, D., Ozkaya, D., Quinn, P. D. & Schuster, M. E. (2022). A cell design for correlative hard X-ray nanoprobe and electron microscopy studies of catalysts under in situ conditions. *J. Synchrotron Rad.* 29, 431.

13. van de Kerkhof, G. T., Walker, J. M., Agrawal, S., Clarke, S. M., Sk, M. H., Craske, D. J., ... Parker, J. E. (2023). An in situ liquid environment for synchrotron hard X-ray nanoprobe microscopy. *Materials at High Temperatures*, 40(4), 371–375.

14. Das, S., Kahnt, M., Valen, Y., Bergh, T., Blomberg, S., Lyubomirskiy, M., Schroer, C., Venvik, H., and Sheppard, T. (2024). Restructuring of Ag catalysts for methanol to formaldehyde conversion studied using in situ X-ray ptychography and electron microscopy. *Catalysis Science & Technology*. 14. 10.1039/D4CY00770K.

15. Julio C. da Silva, Alexandra Pacureanu, Yang Yang, Florin Fus, Maxime Hubert, Leonid Bloch, Murielle Salome, Sylvain Bohic, Peter Cloetens, "High-energy cryo x-ray nano-imaging at the ID16A beamline of ESRF," *Proc. SPIE 10389, X-Ray Nanoimaging: Instruments and Methods III*, 103890F (7 September 2017)

16. Quinn, P. D., Alianelli, L., Gomez-Gonzalez, M., Mahoney, D., Cacho-Nerin, F., Peach, A. & Parker, J. E. (2021). The Hard X-ray Nanoprobe beamline at Diamond Light Source. *J. Synchrotron Rad.* 28, 1006.

17. R. P. Winarski, M. V. Holt, V. Rose, P. Fuesz, D. Carbaugh, C. Benson, D. Shu, et al., A hard x-ray nanoprobe beamline for nanoscale microscopy, *J. Synchrotron Radiation* 19, p. 1056-1060, 2012.



18. A. Somogyi, C. M. Kewish, M. Ribbens, T. Moreno, F. Polack, G. Baranton, K. Desjardins, J. P. Samama, Status of the nanoscopy scanning hard x-ray nanoprobe beamline of Synchrotron SOLEIL, J. Phys: Conf. Ser. 463, p. 012027, 2013
DOI: 10.1039/D5FD00037H
19. S. Chen, J. Deng, Y. Yuan, C. Flachenecker, R. Mak, B. Homberger, Q. Jin, et al., The bionanoprobe: hard x-ray fluorescence nanoprobe with cryogenic capabilities, J. Synchrotron Radiation 21, p. 66-75, 2014.
20. Nazaretski, E., Yan, H., Lauer, K., Bouet, N., Huang, X., Xu, W., Zhou, J., Shu, D., Hwu, Y. and Chu, Y.S. (2017), Design and performance of an X-ray scanning microscope at the Hard X-ray Nanoprobe beamline of NSLS-II. J. Synchrotron Rad., 24: 1113-111
21. Johansson, U., Carbone, D., Kalbfleisch, S., Bjorling, A., Kahnt, M., Sala, S., Stankevici, T., Liebi, M., Rodriguez Fernandez, A., Bring, B., Paterson, D., Thanell, K., Bell, P., Erb, D., Weninger, C., Matej, Z., Roslund, L., Åhnberg, K., Norsk Jensen, B., Tarawneh, H., Mikkelsen, A. & Vogt, U. (2021). NanoMAX: the hard X-ray nanoprobe beamline at the MAX IV Laboratory. J. Synchrotron Rad. 28, 1935-1947.
22. Bajt, S., Prasciolu, M., Fleckenstein, H. et al. X-ray focusing with efficient high-NA multilayer Laue lenses. Light Sci Appl 7, 17162 (2018).
23. Jens Patommel, Susanne Klare, Robert Hoppe, Stephan Ritter, Dirk Samberg, Felix Wittwer, Andreas Jahn, Karola Richter, Christian Wenzel, Johann W. Barth, Maria Scholz, Frank Seiboth, Ulrike Boesenberg, Gerald Falkenberg, Christian G. Schroer; Focusing hard x rays beyond the critical angle of total reflection by adiabatically focusing lenses. Appl. Phys. Lett. 6 March 2017; 110 (10): 101103
24. H. Mimura, S. Handa, T. Kimura, H. Yumoto, D. Yamakawa, H. Yokoyama, S. Matsuyama K. Inagaki, K. Yamamura, Y. Sano et al., Nat. Phys. 6, 122 (2010)
25. Kruger, S. P., Neubauer, H., Bartels, M., Kalbfleisch, S., Giewekemeyer, K., Wilbrandt, P. J., Sprung, M. & Salditt, T. (2012). Sub-10nm beam confinement by X-ray waveguides: design, fabrication and characterization of optical properties. J. Synchrotron Rad. 19, 227-236.
26. Quinn, P. D., Cacho-Nerin, F., Gomez-Gonzalez, M. A., Parker, J. E., Poon, T. & Walker, J. M. (2023). Differential phase contrast for quantitative imaging and spectro-microscopy at a nanoprobe beamline. J. Synchrotron Rad. 30, 200-207.
27. Bolitho EM, Sanchez-Cano C, Shi H, et al. Single-Cell Chemistry of Photoactivatable Platinum Anticancer Complexes. J Am Chem Soc. 2021;143(48):20224-20240.
28. F. Fus, Y. Yang, H. Z. S. Lee, S. Top, M. Carriere, A. Bouron, A. Pacureanu, J. C. da Silva, M. Salmain, A. Vessières, P. Cloetens, G. Jaouen, S. Bohic, Angew. Chem. Int. Ed. 2019, 58, 3461.
29. Paul D. Quinn, Malena Sabaté Landman, Tom Davis, Melina Freitag, Silvia Gazzola, and Sergey Dolgov, Optimal Sparse Energy Sampling for X-ray Spectro-Microscopy: Reducing the X-ray Dose and Experiment Time Using Model Order Reduction, Chemical & Biomedical Imaging 2024 2 (4), 283-292.
30. Oliver Townsend, Silvia Gazzola, Sergey Dolgov, and Paul Quinn, "Undersampling raster scans in spectromicroscopy for a reduced dose and faster measurements," Opt. Express 30, 43237-43254 (2022).
31. Pfeiffer, F. X-ray ptychography. Nature Photon 12, 9–17 (2018).
32. Batey, D., Rau, C. & Cipiccia, S. High-speed X-ray ptychographic tomography. Sci Rep 12, 7846 (2022).



33. Junjing Deng et al., Correlative 3D x-ray fluorescence and ptychographic tomography of frozen-hydrated green algae. *Sci. Adv.* 4, eaau4548 (2018)

View Article Online
DOI: 10.1039/D5FD00037H

34. Koen W. Bossers, Roozbeh Valadian, Silvia Zanoni, Remy Smeets, Nic Friederichs, Jan Garrevoet, Florian Meirer, and Bert M. Weckhuysen, Correlated X-ray Ptychography and Fluorescence Nano-Tomography on the Fragmentation Behavior of an Individual Catalyst Particle during the Early Stages of Olefin Polymerization, *Journal of the American Chemical Society* 2020 142 (8), 3691-3695.

35. T. M. M. Heenan, A. Wade, C. Tan, J. E. Parker, D. Matras, A. S. Leach, J. B. Robinson, A. Llewellyn, A. Dimitrijevic, R. Jervis, P. D. Quinn, D. J. L. Brett, P. R. Shearing, Identifying the Origins of Microstructural Defects Such as Cracking within Ni-Rich NMC811 Cathode Particles for Lithium-Ion Batteries. *Adv. Energy Mater.* 2020, 10, 2002655.

36. Frédérique T.H. Broers et al., Correlated x-ray fluorescence and ptychographic nano-tomography on Rembrandt's The Night Watch reveals unknown lead "layer". *Sci. Adv.* 9, eadj9394 (2023).

37. Jon Kelly, Andrew Male, Nicholas Rubies, David Mahoney, Jessica M. Walker, Miguel A. Gomez-Gonzalez, Guy Wilkin, Julia E. Parker, Paul D. Quinn; The Delta Robot—A long travel nano-positioning stage for scanning x-ray microscopy. *Rev. Sci. Instrum.* 1 April 2022; 93 (4): 043712

38. Cyril Besnard, Ali Marie, Sisini Sasidharan, Petr Buček, Jessica M. Walker, Julia E. Parker, Matthew C. Spink, Robert A. Harper, Shashidhara Marathe, Kaz Wanelik, Thomas E.J. Moxham, Enrico Salvati, Konstantin Ignatyev, Michał M. Kłosowski, Richard M. Shelton, Gabriel Landini, and Alexander M. Korsunsky., Multi-resolution Correlative Ultrastructural and Chemical Analysis of Carious Enamel by Scanning Microscopy and Tomographic Imaging *ACS Applied Materials & Interfaces* 2023 15 (31), 37259-37273.

39. Cyril Besnard, Ali Marie, Sisini Sasidharan, Petr Buček, Jessica M. Walker, Julia E. Parker, Thomas E.J. Moxham, Benedikt Daurer, Burkhard Kaulich, Majid Kazemian, Richard M. Shelton, Gabriel Landini, Alexander M. Korsunsky, Nanoscale correlative X-ray spectroscopy and ptychography of carious dental enamel, *Materials & Design* (2022), 224, 111272.

40. Wilmers, Jana; Bargmann, Swantje, *Acta Biomaterialia* (2020), 107, 1.

41. W. M. Balch The Ecology, Biogeochemistry, and Optical Properties of Coccolithophores, *Annu. Rev. Mar. Sci.*, 2018, 3, 71 —98

42. Jessica M. Walker, Hallam J. M. Greene, Yousef Moazzam, Paul D. Quinn, Julia E. Parker and Gerald Langer, *Environ. Sci.: Processes Impacts*, 2024, 26, 966-974.

43. Chevrier, D.M., Cerdá-Doñate, E., Park, Y., Cacho-Nerin, F., Gomez-Gonzalez, M., Uebe, R. and Faivre, D. (2022), Synchrotron-Based Nano-X-Ray Absorption Near-Edge Structure Revealing Intracellular Heterogeneity of Iron Species in Magnetotactic Bacteria. *Small Sci.*, 2: 2100089.

44. Amor, M., Mathon, F.P., Monteil, C.L., Busigny, V. and Lefevre, C.T. (2020), Iron-biomineralizing organelle in magnetotactic bacteria: function, synthesis and preservation in ancient rock samples. *Environ Microbiol.* 22: 3611-3632.

45. Wang, X., Yang, J., Andrei, C. et al. Biomineralization of calcium phosphate revealed by in situ liquid-phase electron microscopy. *Commun Chem* 1, 80 (2018).

46. Kun He et al., Revealing nanoscale mineralization pathways of hydroxyapatite using in situ liquid cell transmission electron microscopy. *Sci. Adv.* 6, eaaz7524 (2020).



47. L.-A. DiCecco, T. Tang, E. D. Sone, K. Grandfield, Exploring Biomineralization Processes Using In Situ Liquid Transmission Electron Microscopy: A Review. *Small* 2024, 21, 2407539. View Article Online
DOI: 10.1039/D5FD00037H
48. Liza-Anastasia DiCecco, Ruixin Gao, Jennifer L. Gray, Deborah F. Kelly, Eli D. Sone, and Kathryn Grandfield, Liquid Transmission Electron Microscopy for Probing Collagen Biomineralization, *Nano Letters* 2023 23 (21), 9760-9768.
49. Biao Jin, Zhaoming Liu, Changyu Shao, Jiajun Chen, Lili Liu, Ruikang Tang, and James J. De Yoreo, Phase Transformation Mechanism of Amorphous Calcium Phosphate to Hydroxyapatite Investigated by Liquid-Cell Transmission Electron Microscopy, *Crystal Growth & Design* 2021 21 (9), 5126-5134
50. J.D. Currey, *Form and Function*, Academic Press (1988) 11,183-210.
51. B. Chen, X. Peng, J.G. Wang, X. Wu, Laminated microstructure of Bivalva shell and research of biomimetic ceramic/polymer composite, *Ceramics International*,2004, 30(7)2011-2014.
52. M. Holler, J. Raabe, R. Wepf, S. H. Shahmoradian, A. Diaz, B. Sarafimov, T. Lachat, H. Walther, M. Vitins; OMNY PIN—A versatile sample holder for tomographic measurements at room and cryogenic temperatures. *Rev. Sci. Instrum.* 2017; 88 (11): 113701.
53. M. Holler et al., An instrument for 3D x-ray nano-imaging, *Rev. Sci. Instrum.* 83, 073703 (2012)
54. Pierre Thibault, Martin Dierolf, Oliver Bunk, Andreas Menzel, Franz Pfeiffer, Probe retrieval in ptychographic coherent diffractive imaging, *Ultramicroscopy*,2009 109(4) 338-343.
55. P Thibault and M Guizar-Sicairos Maximum-likelihood refinement for coherent diffractive imaging, 2012 *New J. Phys.* 14 063004.
56. Bayerlein, B., Zaslansky, P., Dauphin, Y. et al. Self-similar mesostructure evolution of the growing mollusc shell reminiscent of thermodynamically driven grain growth. *Nature Mater* 13, 1102–1107 (2014).
57. Jean-Pierre Cuif, Oulfa Belhadj, Stephan Borensztajn, Marc Gèze, Sergio Trigos-Santos, Patricia Prado, Yannicke Dauphin, Prism substructures in the shell of *Pinna nobilis* (Linnaeus, 1758), *Mollusca – Evidence for a three-dimensional pulsed-growth model*, *Heliyon*, 6 (7) 2020, e04513.
58. Fabio Nudelman, Hong H. Chen, Harvey A. Goldberg, Steve Weiner and Lia Addadi, Lessons from biomineralization: comparing the growth strategies of mollusc shell prismatic and nacreous layers in *Atrina rigida*, *Faraday Discuss.*, 2007,136, 9-25.
59. Schenk AS, Kim Y-Y. Unraveling the internal microstructure of biogenic and bioinspired calcite single crystals. *MRS Bulletin*. 2015;40(6):499–508. doi:10.1557/mrs.2015.100
60. Antonio Gerardo Checa, Alejandro B. Rodríguez-Navarro, Fransico J. Esteban-Delgado, The nature and formation of calcitic columnar prismatic shell layers in pteriomorphian bivalves, *Biomaterials*,26 (32) 2005, 6404-6414,



Figures

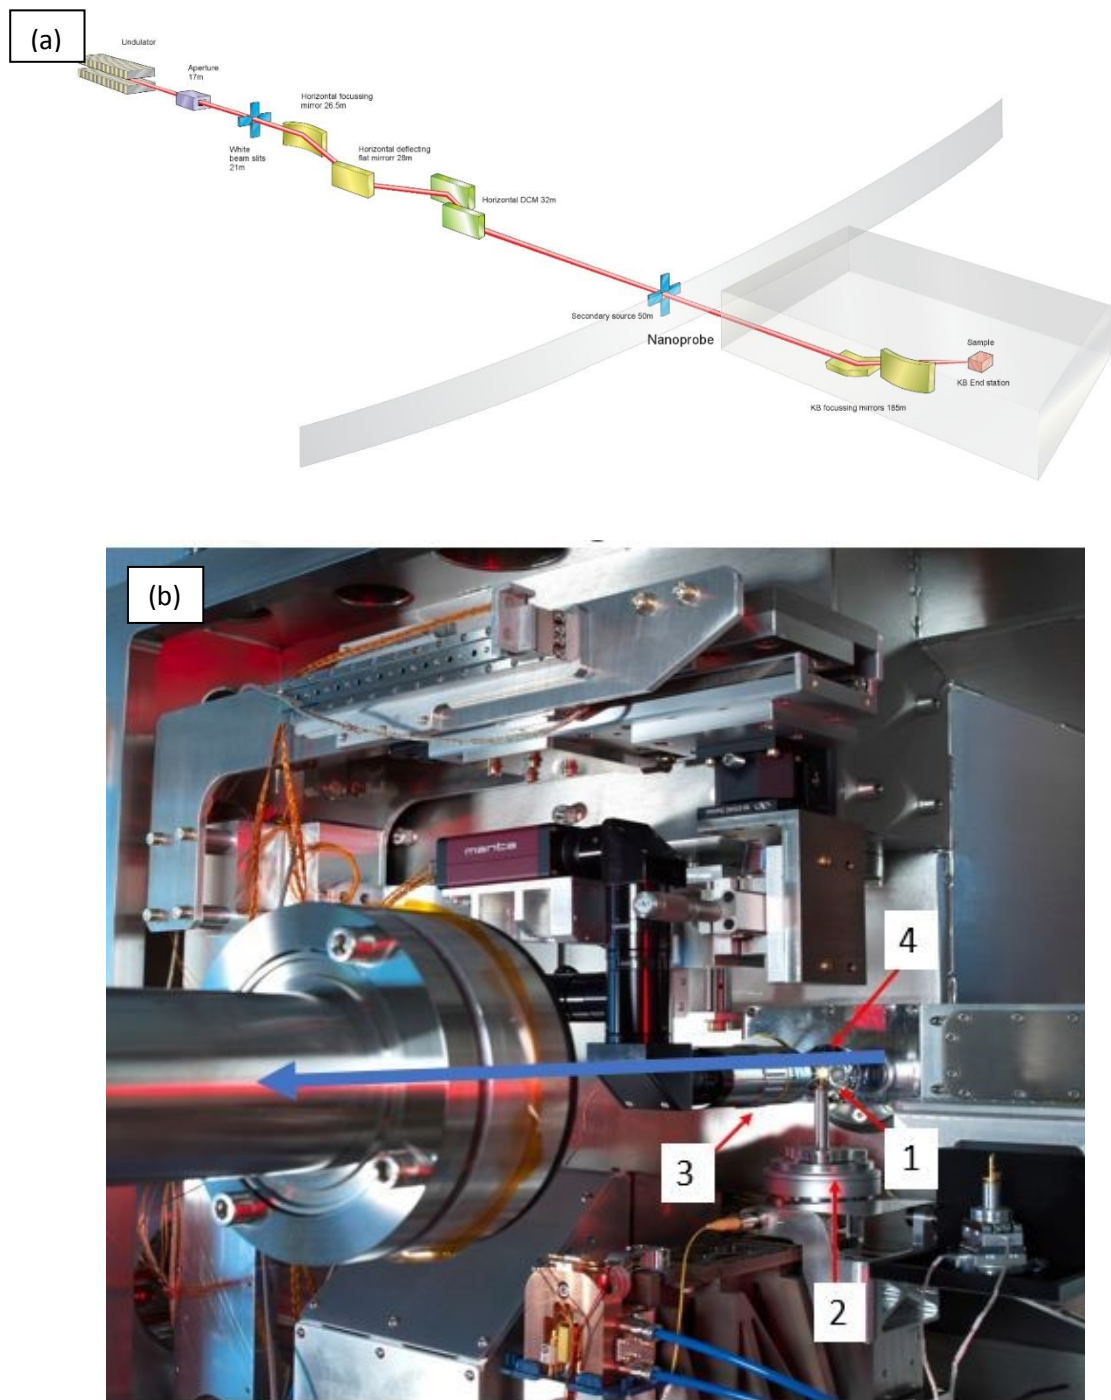


Figure 1 (a) A schematic of the I14 Hard X-ray Nanoprobe beamline layout showing the major components. (b) Inside the I14 Hard X-ray Nanoprobe experimental hutch showing the endstation, the blue arrow indicates the X-ray beam direction. 1-4 show the position of 1. The sample mounting position. 2. Scanning and rotation stages. 3. Sample alignment microscope. 4. Four-element silicon drift detector (XRF detector).



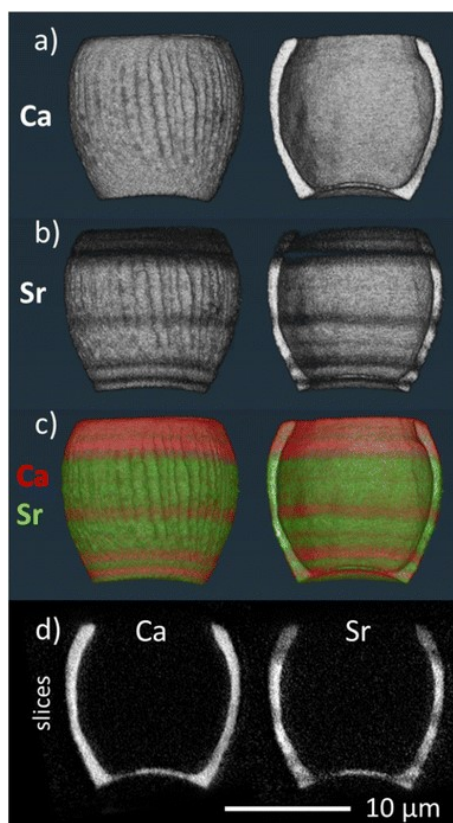


Figure 2 3D volume renderings of the reconstructed 3D XRF data for (a) calcium and (b) strontium signals individually and (c) combined (calcium signal in red, strontium signal in green), showing both the full image of the lopadolith and a cut through along the growth direction. The corresponding reconstruction slices are also shown (d). Reproduced from reference 42 with permission from the Royal Society of Chemistry.

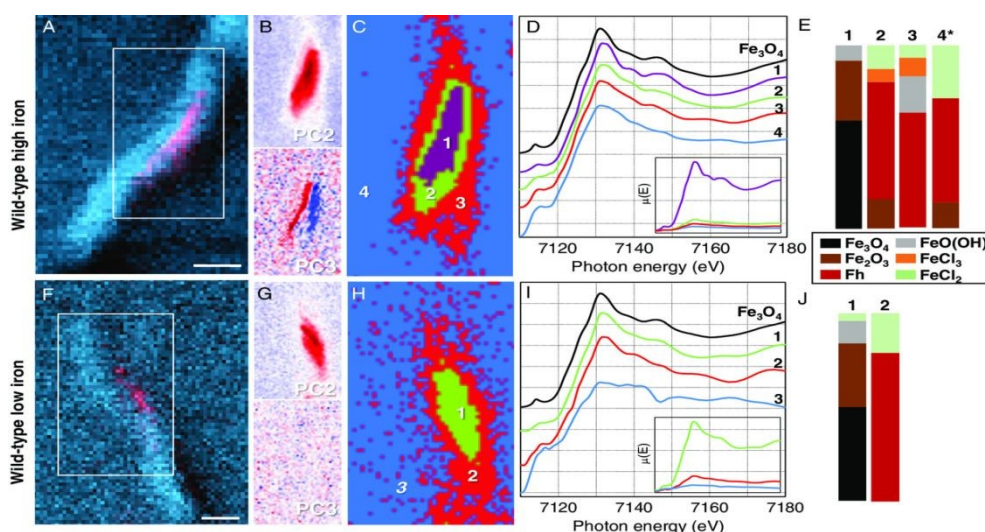


Figure 3 Nano-XANES data for MTB with complete magnetosome chains. A, F) WT-high-iron and WT-low-iron nano-XANES regions (white box), B, G) PCA maps (red signal), C, H) maps of cluster centers, D, I) normalized offset Fe K-edge XANES spectra (inset with normalized spectra retaining edge jump



values), and E,J) a summarized composite of LC fitting results. Reproduced from reference 43 under creative commons CC BY 4.0 licence

View Article Online
DOI: 10.1039/D5FD00037H

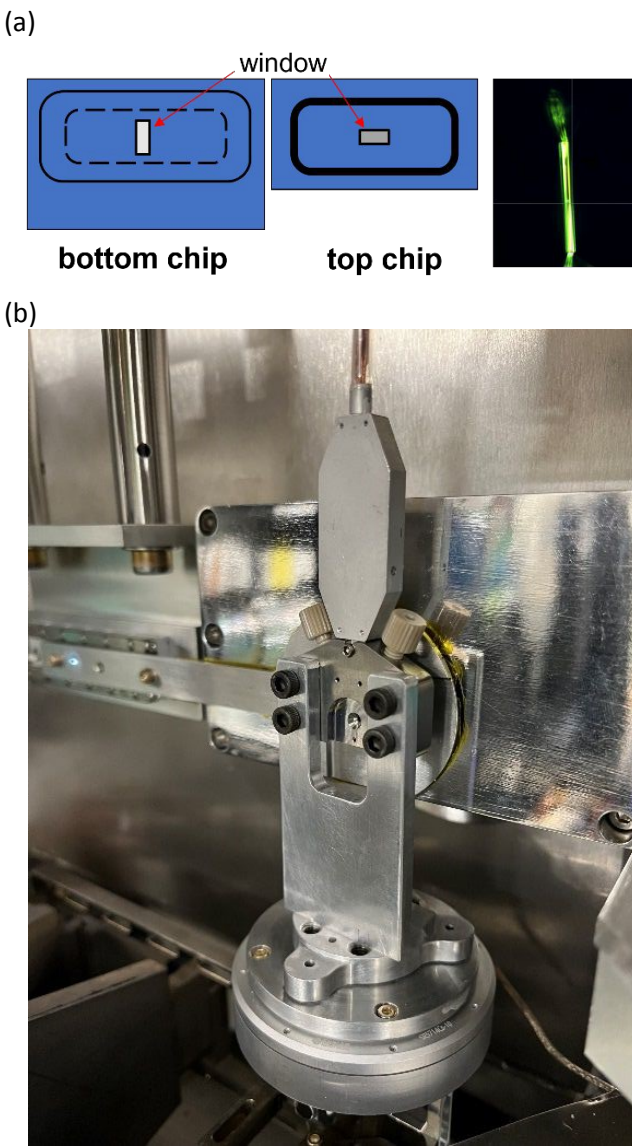


Figure 4 (a) Sketch of MEMS liquid nanochip assembly showing the (left) bottom and top chip silicon nitride windows (perpendicular to each other), when assembled and mounted on the beamline the window area can be observed in the sample microscope (right) The windows are 50 μm in width, **(b)** Assembled chip mounted in a liquid cell on I14 endstation



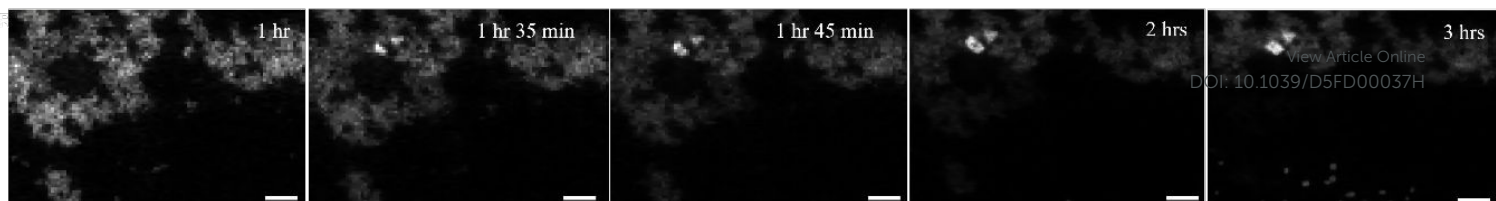


Figure 5 Ca-K α fluorescence maps extracted from n-XRF spectra at different time points during in situ CaP crystallisation in a liquid cell. scale bar = 500nm

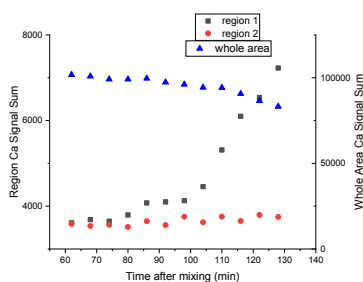
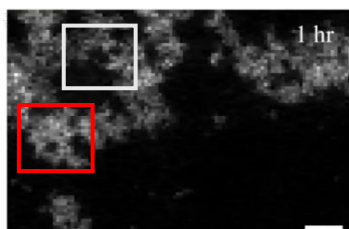


Figure 6 (a) Ca-K α XRF map indicating the location of Region 1 (white box) and region 2 (red box) (b) The total Ca signal in Region 1, Region 2 and the whole mapped area as a function of time

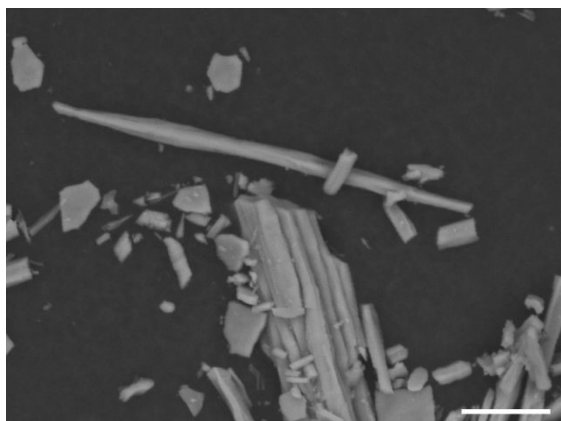


Figure 7 SEM image of calcite prisms from *M. edulis* after dissolution of interprismatic organic matrix. Scale bar 10 um



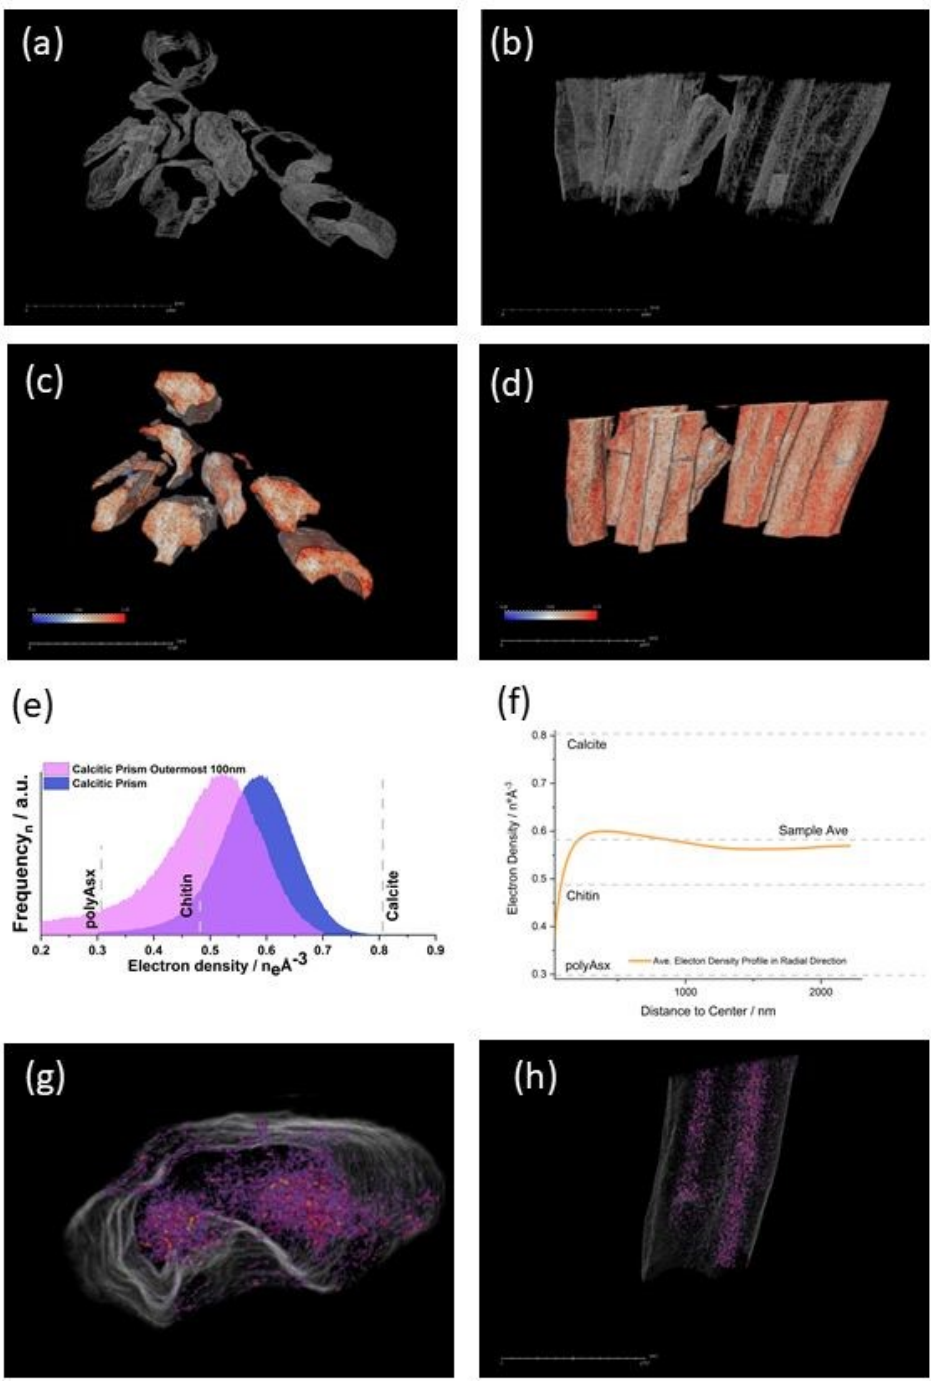


Figure 8 Segmentation of the 3D volume reconstruction to show (a) and (b) the outermost 100nm, (c) and (d) the rest of the prism, (e) the histogram of electron density for the prism and outermost 100nm (f) the variation in electron density with distance from the centre of a prism. (g) and (h) volume segmentation of the voxels where the organic content was calculated to be 55-75%

